



LEXAN™ Resin 9945A

Americas: COMMERCIAL

Lexan* resin 9945A Polycarbonate (PC) is a non-filled, injection moldable grade. This non-chlorinated, non-brominated PC has an UL-94 V0 rating at 1.8 mm. Lexan resin 9945A is available in clear transparent only and is a general-purpose resin intended for thin wall applications.

TYPICAL PROPERTIES ¹	TYPICAL VALUE	Unit	Standard
MECHANICAL			
Tensile Stress, yld, Type I, 50 mm/min	650	kgf/cm ²	ASTM D 638
Tensile Stress, brk, Type I, 50 mm/min	670	kgf/cm ²	ASTM D 638
Tensile Strain, yld, Type I, 50 mm/min	6	%	ASTM D 638
Tensile Strain, brk, Type I, 50 mm/min	120	%	ASTM D 638
Tensile Modulus, 5 mm/min	24200	kgf/cm ²	ASTM D 638
Flexural Stress, yld, 1.3 mm/min, 50 mm span	1040	kgf/cm ²	ASTM D 790
Flexural Modulus, 1.3 mm/min, 50 mm span	24900	kgf/cm ²	ASTM D 790
Tensile Stress, yield, 50 mm/min	63	MPa	ISO 527
Tensile Stress, break, 50 mm/min	65	MPa	ISO 527
Tensile Strain, yield, 50 mm/min	6	%	ISO 527
Tensile Strain, break, 50 mm/min	100	%	ISO 527
Tensile Modulus, 1 mm/min	2350	MPa	ISO 527
Flexural Stress, yield, 2 mm/min	90	MPa	ISO 178
Flexural Modulus, 2 mm/min	2300	MPa	ISO 178
Hardness, H358/30	95	MPa	ISO 2039-1
IMPACT			
Izod Impact, notched, 23°C	83	cm-kgf/cm	ASTM D 256
Izod Impact, notched, -30°C	11	cm-kgf/cm	ASTM D 256
Instrumented Impact Total Energy, 23°C	805	cm-kgf	ASTM D 3763
Izod Impact, unnotched 80*10*3 +23°C	NB	kJ/m ²	ISO 180/1U
Izod Impact, unnotched 80*10*3 -30°C	NB	kJ/m ²	ISO 180/1U
Izod Impact, notched 80*10*3 +23°C	70	kJ/m ²	ISO 180/1A



LEXAN™ Resin 9945A
Americas: COMMERCIAL

TYPICAL PROPERTIES ¹	TYPICAL VALUE	Unit	Standard
IMPACT			
Izod Impact, notched 80*10*3 -30°C	12	kJ/m ²	ISO 180/1A
Charpy 23°C, V-notch Edgew 80*10*3 sp=62mm	73	kJ/m ²	ISO 179/1eA
Charpy -30°C, V-notch Edgew 80*10*3 sp=62mm	14	kJ/m ²	ISO 179/1eA
Charpy 23°C, Unnotch Edgew 80*10*3 sp=62mm	NB	kJ/m ²	ISO 179/1eU
Charpy -30°C, Unnotch Edgew 80*10*3 sp=62mm	NB	kJ/m ²	ISO 179/1eU
THERMAL			
Vicat Softening Temp, Rate B/50	143	°C	ASTM D 1525
HDT, 0.45 MPa, 3.2 mm, unannealed	138	°C	ASTM D 648
HDT, 1.82 MPa, 3.2mm, unannealed	127	°C	ASTM D 648
CTE, -40°C to 40°C, flow	6.8E-05	1/°C	ASTM E 831
CTE, -40°C to 40°C, xflow	7.3E-05	1/°C	ASTM E 831
Thermal Conductivity	0.2	W/m-°C	ISO 8302
CTE, 23°C to 80°C, flow	7.E-05	1/°C	ISO 11359-2
CTE, 23°C to 80°C, xflow	7.E-05	1/°C	ISO 11359-2
Ball Pressure Test, 125°C +/- 2°C	PASSES	-	IEC 60695-10-2
Vicat Softening Temp, Rate B/50	141	°C	ISO 306
Vicat Softening Temp, Rate B/120	142	°C	ISO 306
HDT/Be, 0.45MPa Edgew 120*10*4 sp=100mm	136	°C	ISO 75/Be
HDT/Ae, 1.8 MPa Edgew 120*10*4 sp=100mm	125	°C	ISO 75/Ae
PHYSICAL			
Specific Gravity	1.2	-	ASTM D 792
Mold Shrinkage, flow, 3.2 mm (5)	0.5 - 0.7	%	SABIC Method
Mold Shrinkage, xflow, 3.2 mm (5)	0.5 - 0.7	%	SABIC Method
Melt Flow Rate, 300°C/1.2 kgf	10	g/10 min	ASTM D 1238
Density	1.2	g/cm ³	ISO 1183



LEXAN™ Resin 9945A
Americas: COMMERCIAL

TYPICAL PROPERTIES ¹	TYPICAL VALUE	Unit	Standard
PHYSICAL			
Water Absorption, (23°C/sat)	0.35	%	ISO 62
Moisture Absorption (23°C / 50% RH)	0.15	%	ISO 62
OPTICAL			
Light Transmission, 2.54 mm	88	%	ASTM D 1003
Haze, 2.54 mm	1	%	ASTM D 1003
ELECTRICAL			
Volume Resistivity	>1.E+15	Ohm-cm	IEC 60093
Surface Resistivity, ROA	>1.E+15	Ohm	IEC 60093
Dielectric Strength, in oil, 3.2 mm	17	kV/mm	IEC 60243-1
Relative Permittivity, 1 MHz	2.7	-	IEC 60250
Dissipation Factor, 50/60 Hz	0.001	-	IEC 60250
Dissipation Factor, 1 MHz	0.01	-	IEC 60250
Comparative Tracking Index	225	V	IEC 60112
Relative Permittivity, 50/60 Hz	2.7	-	IEC 60250
FLAME CHARACTERISTICS			
UL Recognized, 94V-2 Flame Class Rating (3)	0.8	mm	UL 94
UL Recognized, 94V-0 Flame Class Rating (3)	1.8	mm	UL 94
Glow Wire Flammability Index 960°C, passes at	1	mm	IEC 60695-2-12
Glow Wire Ignitability Temperature, 1.0 mm	850	°C	IEC 60695-2-13
Glow Wire Ignitability Temperature, 3.0 mm	850	°C	IEC 60695-2-13
Oxygen Index (LOI)	35	%	ISO 4589



LEXAN™ Resin 9945A
Americas: COMMERCIAL

PROCESSING PARAMETERS	TYPICAL VALUE	Unit
Injection Molding		
Drying Temperature	120	°C
Drying Time	2 - 4	hrs
Maximum Moisture Content	0.02	%
Melt Temperature	280 - 310	°C
Nozzle Temperature	270 - 290	°C
Front - Zone 3 Temperature	280 - 310	°C
Middle - Zone 2 Temperature	270 - 290	°C
Rear - Zone 1 Temperature	260 - 280	°C
Hopper Temperature	60 - 80	°C
Mold Temperature	80 - 110	°C



LEXAN™ Resin 9945A
Americas: COMMERCIAL


CALCULATED FLOW LENGTH INDICATION

Moldflow® Radial Flow Analysis

LEXAN® 9945A

Melt Temperature : 295°C

Mold Temperature : 95°C

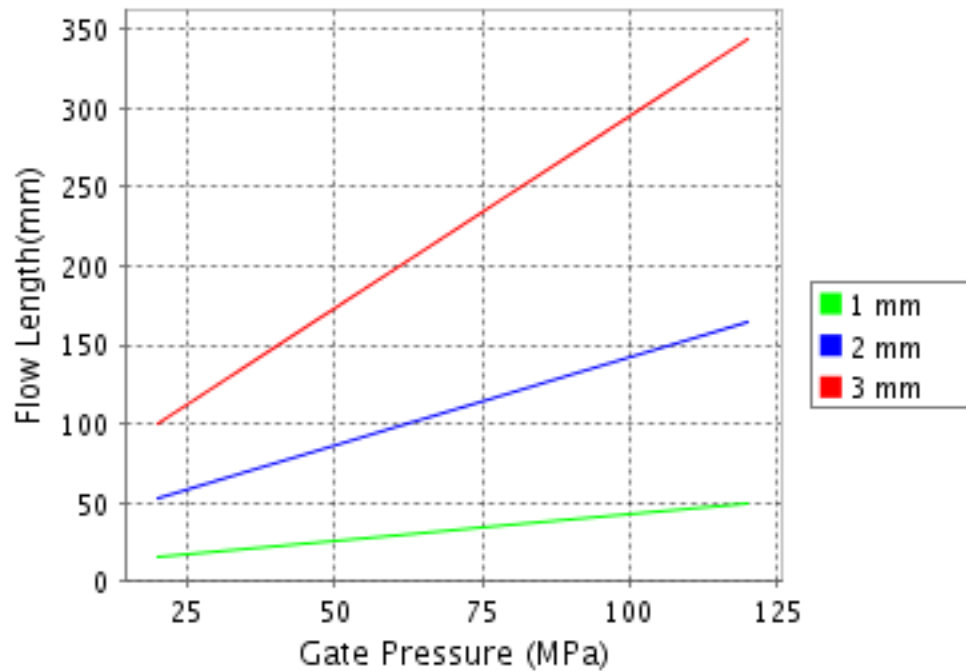

Note: Technical support is recommended if Gate Pressure is greater than 80 MPa. Contact your local representative.

© Moldflow is a registered trademark of the Moldflow Corporation.