



LEXAN™ Resin ML6411

Americas: COMMERCIAL

LEXAN ML6411 polycarbonate (PC) siloxane resin, is a high flow opaque injection molding (IM) grade with very low temperature ductility characteristics. This grade offers UL94 V0 @ 1.5mm and 5VA @ 3.0mm flame retardancy based on non-chlorine, non-bromine FR systems. LEXAN ML6411 resin offers excellent processing characteristics with opportunity for shorter IM cycle times compared to standard PC. This product is available in a wide range of opaque colors and is an excellent candidate for a wide range of electrical applications.

TYPICAL PROPERTIES ¹	TYPICAL VALUE	Unit	Standard
MECHANICAL			
Tensile Stress, yld, Type I, 50 mm/min	630	kgf/cm ²	ASTM D 638
Tensile Stress, brk, Type I, 50 mm/min	550	kgf/cm ²	ASTM D 638
Tensile Strain, yld, Type I, 50 mm/min	5	%	ASTM D 638
Tensile Strain, brk, Type I, 50 mm/min	100	%	ASTM D 638
Tensile Modulus, 50 mm/min	25400	kgf/cm ²	ASTM D 638
Flexural Stress, yld, 1.3 mm/min, 50 mm span	960	kgf/cm ²	ASTM D 790
Flexural Modulus, 1.3 mm/min, 50 mm span	26500	kgf/cm ²	ASTM D 790
Tensile Stress, yield, 50 mm/min	62	MPa	ISO 527
Tensile Stress, break, 50 mm/min	58	MPa	ISO 527
Tensile Strain, yield, 50 mm/min	5	%	ISO 527
Tensile Strain, break, 50 mm/min	100	%	ISO 527
Tensile Modulus, 1 mm/min	2350	MPa	ISO 527
Flexural Stress, yield, 2 mm/min	90	MPa	ISO 178
Flexural Modulus, 2 mm/min	2350	MPa	ISO 178
IMPACT			
Izod Impact, notched, 23°C	91	cm-kgf/cm	ASTM D 256
Izod Impact, notched, -30°C	15	cm-kgf/cm	ASTM D 256
Instrumented Impact Total Energy, 23°C	734	cm-kgf	ASTM D 3763
Izod Impact, notched 80*10*3 +23°C	60	kJ/m ²	ISO 180/1A
Izod Impact, notched 80*10*3 -30°C	15	kJ/m ²	ISO 180/1A
THERMAL			
Vicat Softening Temp, Rate B/50	134	°C	ASTM D 1525
HDT, 1.82 MPa, 3.2mm, unannealed	114	°C	ASTM D 648



LEXAN™ Resin ML6411
Americas: COMMERCIAL

TYPICAL PROPERTIES ¹	TYPICAL VALUE	Unit	Standard
THERMAL			
HDT, 0.45 MPa, 6.4 mm, unannealed	128	°C	ASTM D 648
HDT, 1.82 MPa, 6.4 mm, unannealed	119	°C	ASTM D 648
CTE, -40°C to 40°C, flow	7.7E-05	1/°C	ASTM E 831
CTE, -40°C to 40°C, xflow	5.9E-05	1/°C	ASTM E 831
CTE, -40°C to 40°C, flow	7.E-05	1/°C	ISO 11359-2
CTE, -40°C to 40°C, xflow	7.E-05	1/°C	ISO 11359-2
Ball Pressure Test, 125°C +/- 2°C	PASSES	-	IEC 60695-10-2
Vicat Softening Temp, Rate B/50	134	°C	ISO 306
Vicat Softening Temp, Rate B/120	135	°C	ISO 306
HDT/Be, 0.45MPa Edgew 120*10*4 sp=100mm	125	°C	ISO 75/Be
HDT/Ae, 1.8 MPa Edgew 120*10*4 sp=100mm	115	°C	ISO 75/Ae
Relative Temp Index, Elec	100	°C	UL 746B
Relative Temp Index, Mech w/impact	100	°C	UL 746B
Relative Temp Index, Mech w/o impact	100	°C	UL 746B
PHYSICAL			
Specific Gravity	1.19	-	ASTM D 792
Mold Shrinkage, flow, 3.2 mm (5)	0.4 - 0.8	%	SABIC Method
Melt Flow Rate, 260°C/2.16 kgf	7	g/10 min	ASTM D 1238
Density	1.2	g/cm ³	ISO 1183
Water Absorption, (23°C/sat)	0.3	%	ISO 62
Moisture Absorption (23°C / 50% RH)	0.1	%	ISO 62
Melt Volume Rate, MVR at 260°C/5.0 kg	18	cm ³ /10 min	ISO 1133
ELECTRICAL			
Dielectric Strength, in oil, 3.2 mm	26.5	kV/mm	ASTM D 149
Hot Wire Ignition {PLC}	3	PLC Code	UL 746A



LEXAN™ Resin ML6411
Americas: COMMERCIAL

TYPICAL PROPERTIES ¹	TYPICAL VALUE	Unit	Standard
ELECTRICAL			
High Ampere Arc Ign, surface {PLC}	1	PLC Code	UL 746A
Comparative Tracking Index (UL) {PLC}	2	PLC Code	UL 746A
Volume Resistivity	> 1.E+15	Ohm-cm	IEC 60093
Comparative Tracking Index	250	V	IEC 60112
FLAME CHARACTERISTICS			
UL Compliant, 94-5VA Rating (3)(4)	3	mm	UL 94 by SABIC-IP
UL Recognized, 94V-0 Flame Class Rating (3)	1.5	mm	UL 94
UL Recognized, 94-5VA Rating (3)	3	mm	UL 94
UL Recognized, 94-5VB Rating (3)	2	mm	UL 94
Glow Wire Flammability Index 960°C, passes at	1	mm	IEC 60695-2-12
Glow Wire Ignitability Temperature, 1.0 mm	800	°C	IEC 60695-2-13
Glow Wire Ignitability Temperature, 2.0 mm	800	°C	IEC 60695-2-13
Glow Wire Ignitability Temperature, 3.0 mm	800	°C	IEC 60695-2-13



LEXAN™ Resin ML6411
Americas: COMMERCIAL

PROCESSING PARAMETERS	TYPICAL VALUE	Unit
Injection Molding		
Drying Temperature	90 - 100	°C
Drying Time	2 - 4	hrs
Maximum Moisture Content	0.02	%
Melt Temperature	270 - 300	°C
Nozzle Temperature	250 - 290	°C
Front - Zone 3 Temperature	260 - 300	°C
Middle - Zone 2 Temperature	250 - 290	°C
Rear - Zone 1 Temperature	230 - 260	°C
Hopper Temperature	60 - 80	°C
Mold Temperature	60 - 90	°C



LEXAN™ Resin ML6411
Americas: COMMERCIAL


CALCULATED FLOW LENGTH INDICATION

Moldflow® Radial Flow Analysis

LEXAN® ML6411

Melt Temperature : 285°C

Mold Temperature : 75°C

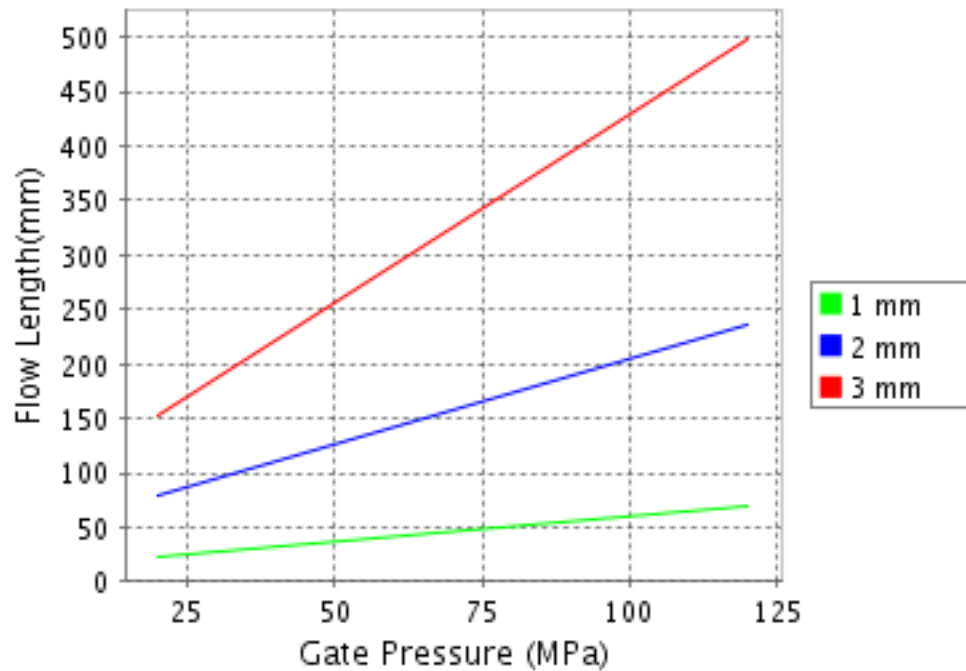

Note: Technical support is recommended if Gate Pressure is greater than 80 MPa. Contact your local representative.

© Moldflow is a registered trademark of the Moldflow Corporation.