

Technical Data Sheet

Schulaketon GF 30 4DE

Polyketone, Aliphatic
LyondellBasell Industries
Engineering Plastics

Product Description
30% glass fiber reinforced aliphatic Polyketone, flame-retardant, halogen free

General		
Filler / Reinforcement	• Glass Fiber, 30% Filler by Weight	
Features	• Flame Retardant • Halogen Free	
UL File Number	• E86615	
Processing Method	• Injection Molding	
Resin ID (ISO 1043)	• PK GF30 FR(40)	

Physical	Nominal Value (English)	Nominal Value (SI)	Test Method
Density	1.47 g/cm ³	1.47 g/cm ³	ISO 1183/A
Melt Volume-Flow Rate (MVR) (240°C/5.0 Kg)	7.0 cm ³ /10min	7.0 cm ³ /10min	ISO 1133

Mechanical	Nominal Value (English)	Nominal Value (SI)	Test Method
Tensile Modulus	1.23E+6 psi	8500 MPa	ISO 527-1/1A/1
Tensile Stress (Break)	18900 psi	130 MPa	ISO 527-2/1A/5
Tensile Strain (Break)	4.5 %	4.5 %	ISO 527-2/1A/5
Flexural Modulus ¹	1.28E+6 psi	8800 MPa	ISO 178
Flexural Stress ¹ (3.5% Strain)	27600 psi	190 MPa	ISO 178

Impact	Nominal Value (English)	Nominal Value (SI)	Test Method
Charpy Notched Impact Strength			ISO 179/1eA
-22°F (-30°C)	3.8 ft·lb/in ²	7.9 kJ/m ²	
73°F (23°C)	6.1 ft·lb/in ²	13 kJ/m ²	
Charpy Unnotched Impact Strength			ISO 179/1eU
-22°F (-30°C)	31 ft·lb/in ²	65 kJ/m ²	
73°F (23°C)	32 ft·lb/in ²	68 kJ/m ²	

Thermal	Nominal Value (English)	Nominal Value (SI)	Test Method
Deflection Temperature Under Load			
66 Psi (0.45 Mpa), Unannealed	419 °F	215 °C	ISO 75-2/Bf
264 Psi (1.8 Mpa), Unannealed	403 °F	206 °C	ISO 75-2/Af

Vicat Softening Temperature			
--	406 °F	208 °C	ISO 306/B50
--	421 °F	216 °C	ISO 306/A50

Ball Pressure Test (266°F (130°C))	Pass	Pass	IEC 60695-10-2
------------------------------------	------	------	----------------

RTI Elec			UL 746B
0.016 In (0.40 Mm)	122 °F	50.0 °C	
0.024 In (0.60 Mm)	122 °F	50.0 °C	
0.031 In (0.8 Mm)	122 °F	50.0 °C	
0.06 In (1.6 Mm)	122 °F	50.0 °C	
0.12 In (3.0 Mm)	122 °F	50.0 °C	

RTI Imp			UL 746B
0.016 In (0.40 Mm)	122 °F	50.0 °C	
0.024 In (0.60 Mm)	122 °F	50.0 °C	
0.031 In (0.8 Mm)	122 °F	50.0 °C	
0.06 In (1.6 Mm)	122 °F	50.0 °C	
0.12 In (3.0 Mm)	122 °F	50.0 °C	

Technical Data Sheet

Schulaketon GF 30 4DE

Polyketone, Aliphatic
LyondellBasell Industries
Engineering Plastics

Thermal	Nominal Value (English)	Nominal Value (SI)	Test Method
RTI Str			UL 746B
0.016 In (0.40 Mm)	122 °F	50.0 °C	
0.024 In (0.60 Mm)	122 °F	50.0 °C	
0.031 In (0.8 Mm)	122 °F	50.0 °C	
0.06 In (1.6 Mm)	122 °F	50.0 °C	
0.12 In (3.0 Mm)	122 °F	50.0 °C	
Electrical	Nominal Value (English)	Nominal Value (SI)	Test Method
Surface Resistivity	> 1.0E+15 ohms	> 1.0E+15 ohms	IEC 60093
Volume Resistivity	> 1.0E+13 ohms·m	> 1.0E+13 ohms·m	IEC 62631-3-1
Electric Strength ²			IEC 60243-1
73°F (23°C), 0.0394 In (1.00 Mm), In Oil	810 V/mil	32 kV/mm	
Comparative Tracking Index	600 V	600 V	IEC 60112
High Amp Arc Ignition (HAI)			UL 746A
0.016 In (0.40 Mm)	PLC 0	PLC 0	
0.024 In (0.60 Mm)	PLC 0	PLC 0	
0.03 In (0.8 Mm)	PLC 0	PLC 0	
0.06 In (1.6 Mm)	PLC 0	PLC 0	
0.12 In (3.0 Mm)	PLC 0	PLC 0	
Hot-wire Ignition (HWI)			UL 746A
0.016 In (0.40 Mm)	PLC 0	PLC 0	
0.024 In (0.60 Mm)	PLC 0	PLC 0	
0.03 In (0.8 Mm)	PLC 0	PLC 0	
0.06 In (1.6 Mm)	PLC 0	PLC 0	
0.12 In (3.0 Mm)	PLC 0	PLC 0	
Flammability	Nominal Value (English)	Nominal Value (SI)	Test Method
Burning Rate			
0.0787 In (2.00 Mm), Self-extinguishing	0.0 in/min	0.0 mm/min	ISO 3795
0.0787 In (2.00 Mm), Self-extinguishing	0.0 in/min	0.0 mm/min	FMVSS 302
Flame Rating			
0.016 In (0.40 Mm)	V-0	V-0	UL 94 IEC 60695-11-10, -20
0.024 In (0.60 Mm)	V-0	V-0	UL 94 IEC 60695-11-10, -20
0.031 In (0.8 Mm)	V-0	V-0	UL 94
0.06 In (1.6 Mm)	• V-0 • 5VA	• V-0 • 5VA	UL 94 IEC 60695-11-10, -20
0.12 In (3.0 Mm)	• V-0 • 5VA	• V-0 • 5VA	UL 94 IEC 60695-11-10, -20
0.03 In (0.8 Mm)	V-0	V-0	IEC 60695-11-10, -20
Glow Wire Flammability Index			IEC 60695-2-12
0.024 In (0.60 Mm)	1760 °F	960 °C	
0.031 In (0.8 Mm)	1760 °F	960 °C	
0.06 In (1.6 Mm)	1760 °F	960 °C	
0.12 In (3.0 Mm)	1760 °F	960 °C	



Technical Data Sheet

Schulaketon GF 30 4DE


Polyketone, Aliphatic
 LyondellBasell Industries
 Engineering Plastics

Flammability	Nominal Value (English)	Nominal Value (SI)	Test Method
Glow Wire Ignition Temperature			IEC 60695-2-13
0.024 In (0.60 Mm)	1520 °F	825 °C	
0.031 In (0.8 Mm)	1520 °F	825 °C	
0.06 In (1.6 Mm)	1560 °F	850 °C	
0.12 In (3.0 Mm)	1520 °F	825 °C	
Oxygen Index	30 %	30 %	ISO 4589-2

Technical Data Sheet

Schulaketon GF 30 4DE

Polyketone, Aliphatic
LyondellBasell Industries
Engineering Plastics

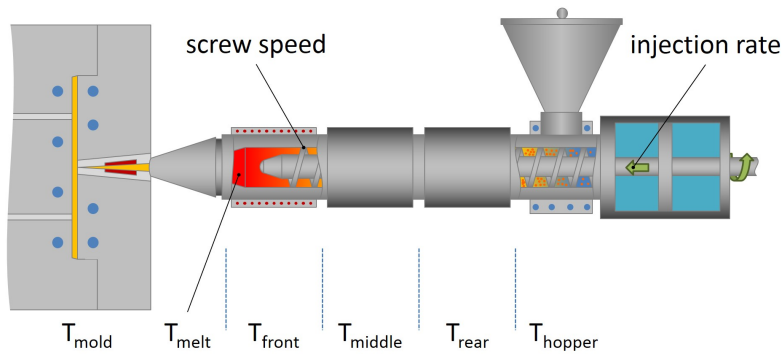

Injection	Nominal Value (English)	Nominal Value (SI)
Drying Temperature	176 °F	80 °C
Drying Time	2.0 to 4.0 hr	2.0 to 4.0 hr
Suggested Max Moisture	0.15 %	0.15 %
Processing (Melt) Temp	446 to 482 °F	230 to 250 °C
Mold Temperature	140 to 212 °F	60 to 100 °C
Injection Rate	Slow-Moderate	Slow-Moderate
Back Pressure	290 to 1160 psi	2.00 to 8.00 MPa
Screw Speed	< 591 in/min	< 15 m/min

Injection Notes

Before start, nozzle, screw, barrel and hot-runner have to be cleaned with Polyolefin. Contamination of other material leads to degradation or crosslinking of SCHULAKETON®.

Avoid shut down for more than 8 minutes at moulding temperature, because of degradation and crosslinking of SCHULAKETON®. Purge with Polyolefin!

Mould surfaces in contact with melt are recommended to be of non-corrosive steel, chrome content >12%

Notes

¹ 0.079 in/min (2.0 mm/min)

² 2000 V/sec

Notes

These are typical property values not to be construed as specification limits.