

# Zytel® BM73G15THS BK317

## NYLON RESIN

Common features of Zytel® nylon resin include mechanical and physical properties such as high mechanical strength, excellent balance of stiffness and toughness, good high temperature performance, good electrical and flammability properties, good abrasion and chemical resistance. In addition, Zytel® nylon resins are available in different modified and reinforced grades to create a wide range of products with tailored properties for specific processes and end-uses. Zytel® nylon resin, including most flame retardant grades, offer the ability to be coloured.

The good melt stability of Zytel® nylon resin normally enables the recycling of properly handled production waste. If recycling is not possible, we recommend, as the preferred option, incineration with energy recovery (-31kJ/g of base polymer) in appropriately equipped installations. For disposal, local regulations have to be observed.

Zytel® nylon resin typically is used in demanding applications in the automotive, furniture, domestic appliances, sporting goods and construction industry.

Zytel® BM73G15THS is a 15% glass fibre reinforced, heat stabilised, lubricated, toughened polyamide 6 for blow moulding.

### Product information

Resin Identification	PA6-IGF15	ISO 1043
Part Marking Code	>PA6-IGF15<	ISO 11469
ISO designation	ISO 16396-PA6-I,GF15,M1CGHR,S14-050	

### Rheological properties

	dry/cond.		
Moulding shrinkage, parallel	0.7/-	%	ISO 294-4, 2577
Moulding shrinkage, normal	1.2/-	%	ISO 294-4, 2577
Melt viscosity , @ 1000 sec-1, 280°C	300/*	Pa.s	ISO 11443

### Typical mechanical properties

	dry/cond.			
Tensile Modulus	5000/2500	MPa		ISO 527-1/-2
Stress at break, 5mm/min	100/65	MPa		ISO 527-1/-2
Strain at break, 5mm/min	4.5/23	%		ISO 527-1/-2
Charpy impact strength, 23°C	80/110	kJ/m <sup>2</sup>		ISO 179/1eU
Charpy notched impact strength, 23°C	21/29	kJ/m <sup>2</sup>		ISO 179/1eA
Charpy notched impact strength, -30°C	13/11	kJ/m <sup>2</sup>		ISO 179/1eA
Charpy notched impact strength, -40°C	12/-	kJ/m <sup>2</sup>		ISO 179/1eA
Izod notched impact strength, 23°C	21/28	kJ/m <sup>2</sup>		ISO 180/1A
Izod notched impact strength, -30°C	11/11	kJ/m <sup>2</sup>		ISO 180/1A
Ball indentation hardness, H 961/30	180/-	MPa		ISO 2039-1
Poisson's ratio	0.35/0.38 <sup>[A]</sup>			

[A]: Assessed

# Zytel® BM73G15THS BK317

## NYLON RESIN

### Thermal properties

	dry/cond.		
Melting temperature, 10°C/min	221/*	°C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	60/10	°C	ISO 11357-1/-3
Temp. of deflection under load, 1.8 MPa	190/*	°C	ISO 75-1/-2
Temp. of deflection under load, 0.45 MPa	215/*	°C	ISO 75-1/-2

### Flammability

	dry/cond.		
Oxygen index	25/*	%	ISO 4589-1/-2
FMVSS Class	B		ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	<80	mm/min	ISO 3795 (FMVSS 302)

### Electrical properties

	dry/cond.		
Dissipation factor, 100Hz	160/-	E-4	IEC 62631-2-1
Dissipation factor, 1MHz	160/-	E-4	IEC 62631-2-1
Volume resistivity	1E13/-	Ohm.m	IEC 62631-3-1
Comparative tracking index	600/-		IEC 60112

### Other properties

	dry/cond.		
Humidity absorption, 2mm	2.6/*[DS]	%	Sim. to ISO 62
Water absorption, 2mm	7.5/*[DS]	%	Sim. to ISO 62
Density	1200/-	kg/m <sup>3</sup>	ISO 1183

[DS]: Derived from similar grade

### Injection

Drying Recommended	yes		
Drying Temperature	80	°C	
Drying Time, Dehumidified Dryer	2 - 4	h	
Processing Moisture Content	≤0.2	%	
Melt Temperature Optimum	270	°C	Internal
Min. melt temperature	260	°C	
Max. melt temperature	280	°C	
Screw tangential speed	≤0.2	m/s	
Mold Temperature Optimum	100	°C	
Min. mould temperature	70	°C	
Max. mould temperature	120	°C	
Hold pressure range	50 - 100	MPa	
Hold pressure time	3	s/mm	

# Zytel® BM73G15THS BK317

## NYLON RESIN

### Extrusion

Drying Temperature	80 °C
Drying Time, Dehumidified Dryer	4 - 6 h
Processing Moisture Content	≤0.06 %
Melt Temperature Range	235 - 250 °C

### Blow Molding

Drying Recommended	yes
Drying Temperature	110 - 120 °C
Drying Time, Dehumidified Dryer	4 - 6 h
Processing Moisture Content	≤0.03 %
Melt Temperature Optimum	260 °C
Melt Temperature Range	255 - 265 °C
Mold Temperature Optimum	90 °C
Mold Temperature Range	80 - 110 °C


### Characteristics

Additives	Release agent
-----------	---------------

# Zytel® BM73G15THS BK317

NYLON RESIN


## Viscosity-shear rate

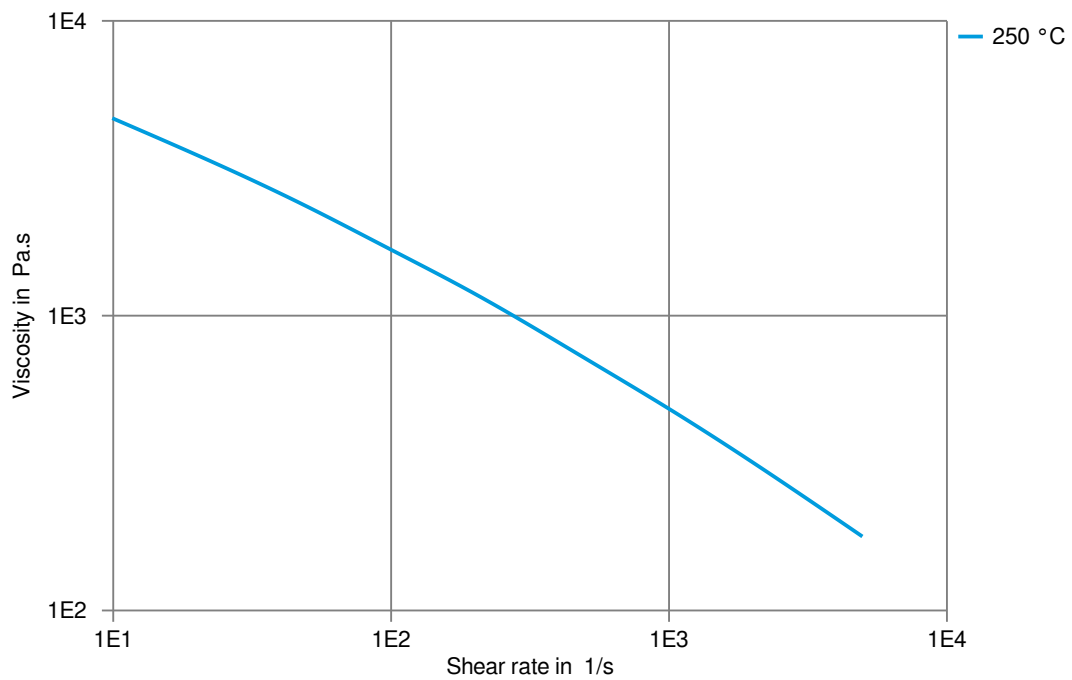

# Zytel® BM73G15THS BK317

NYLON RESIN


## Shearstress-shear rate

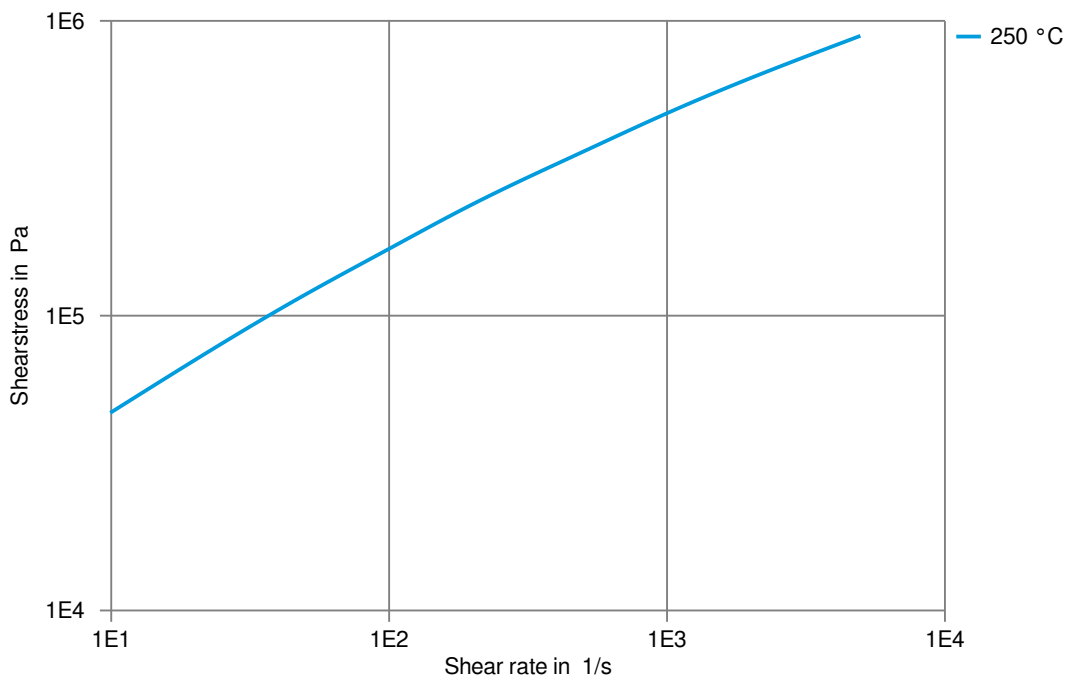

# Zytel® BM73G15THS BK317

NYLON RESIN


## Stress-strain (dry)

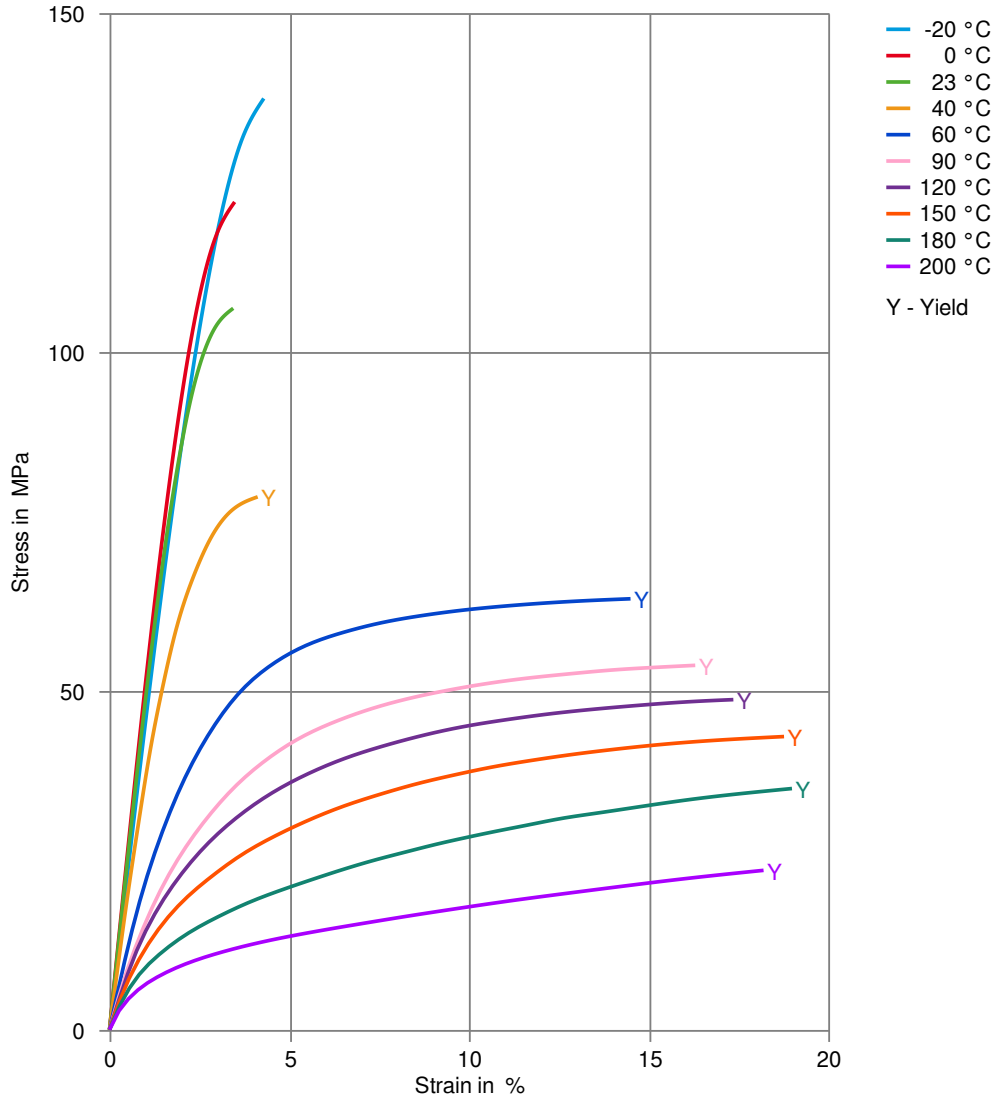

# Zytel® BM73G15THS BK317

NYLON RESIN


## Stress-strain (cond.)

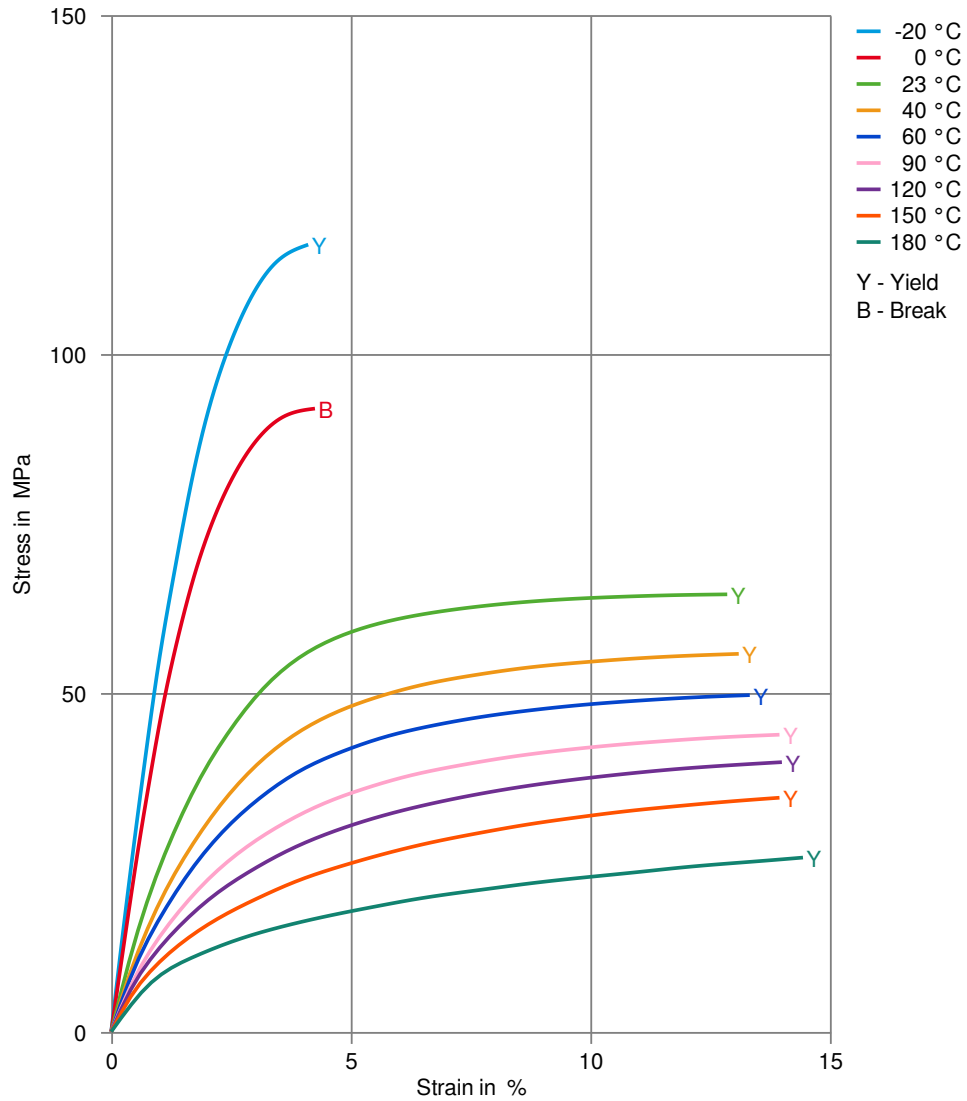

# Zytel® BM73G15THS BK317

NYLON RESIN


## Secant modulus-strain (dry)

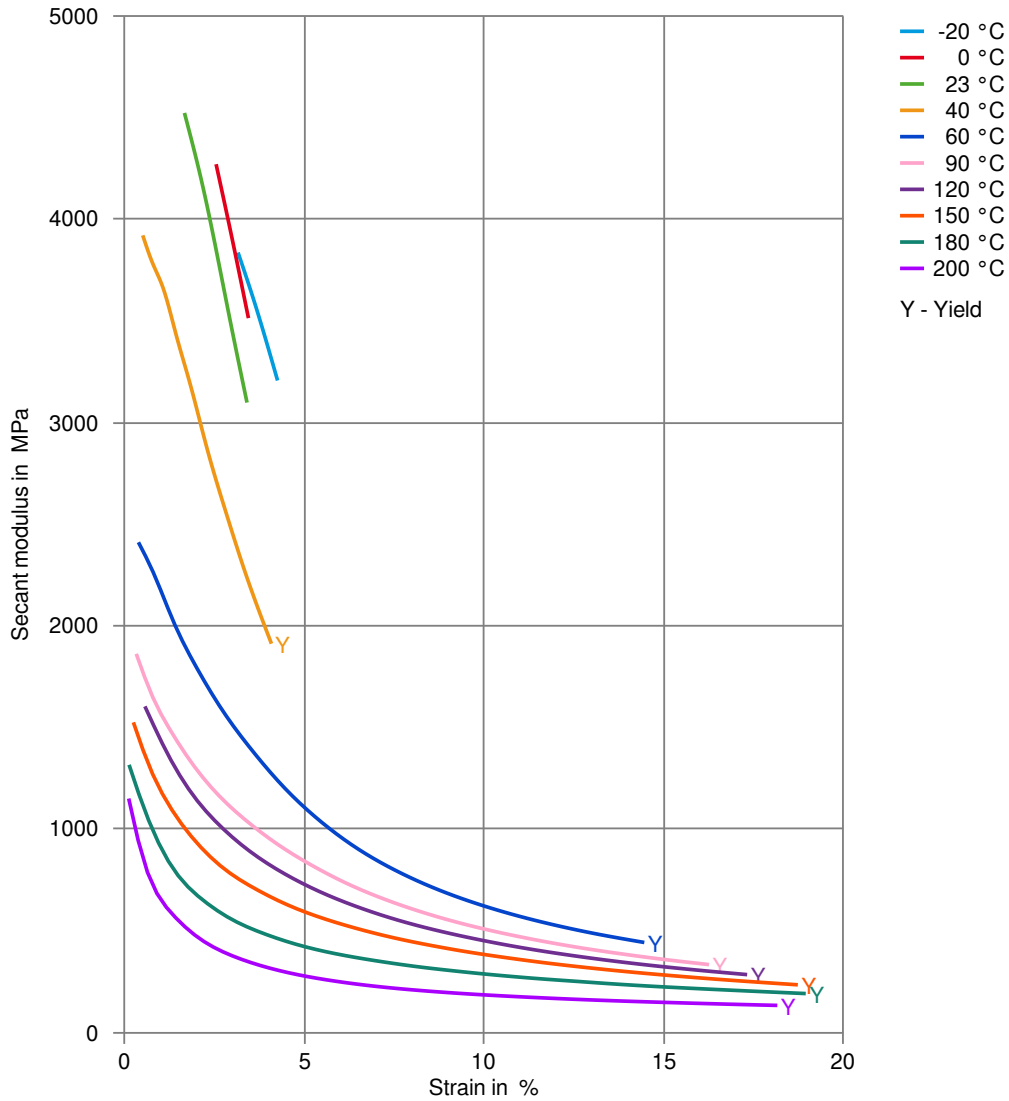

# Zytel® BM73G15THS BK317

NYLON RESIN


## Secant modulus-strain (cond.)

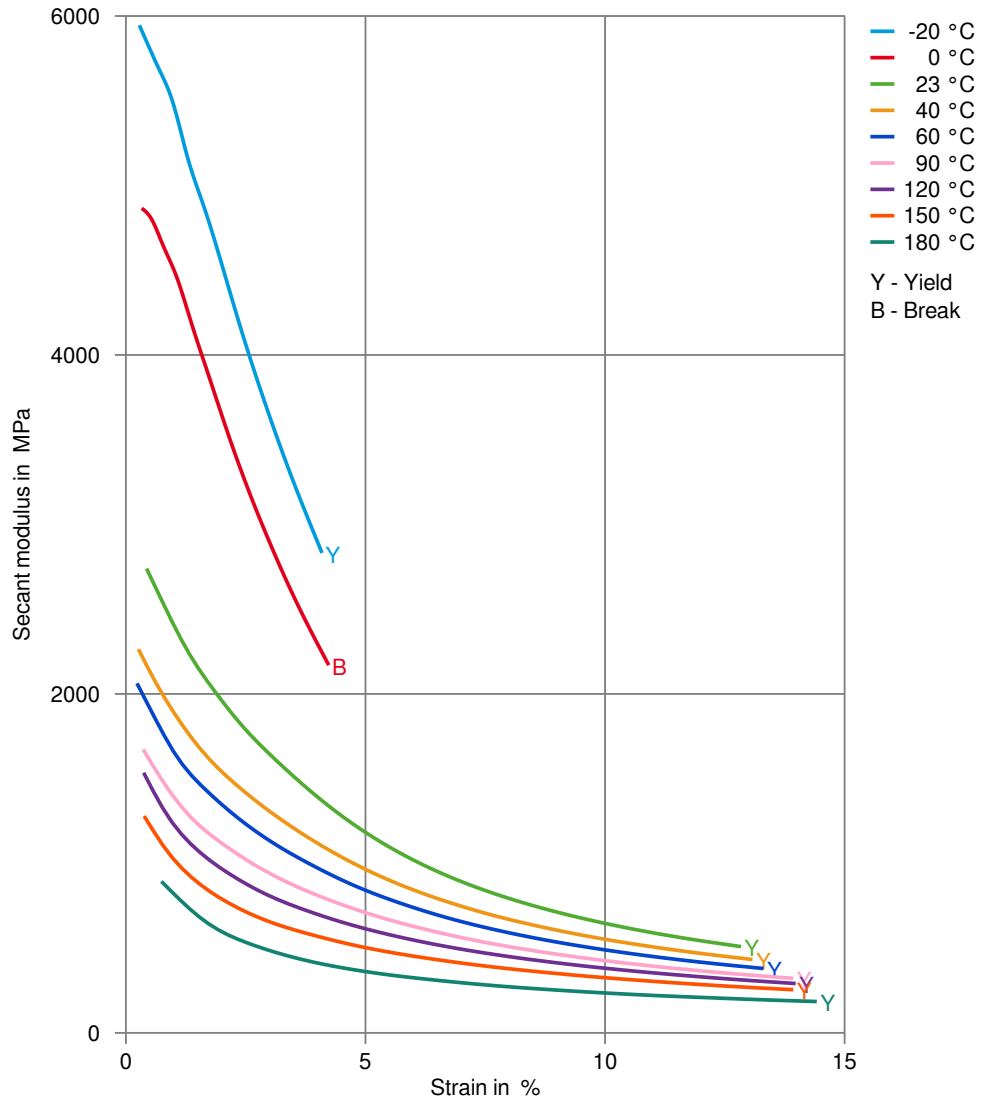

# Zytel® BM73G15THS BK317

NYLON RESIN


Specific volume-temperature (pvT)

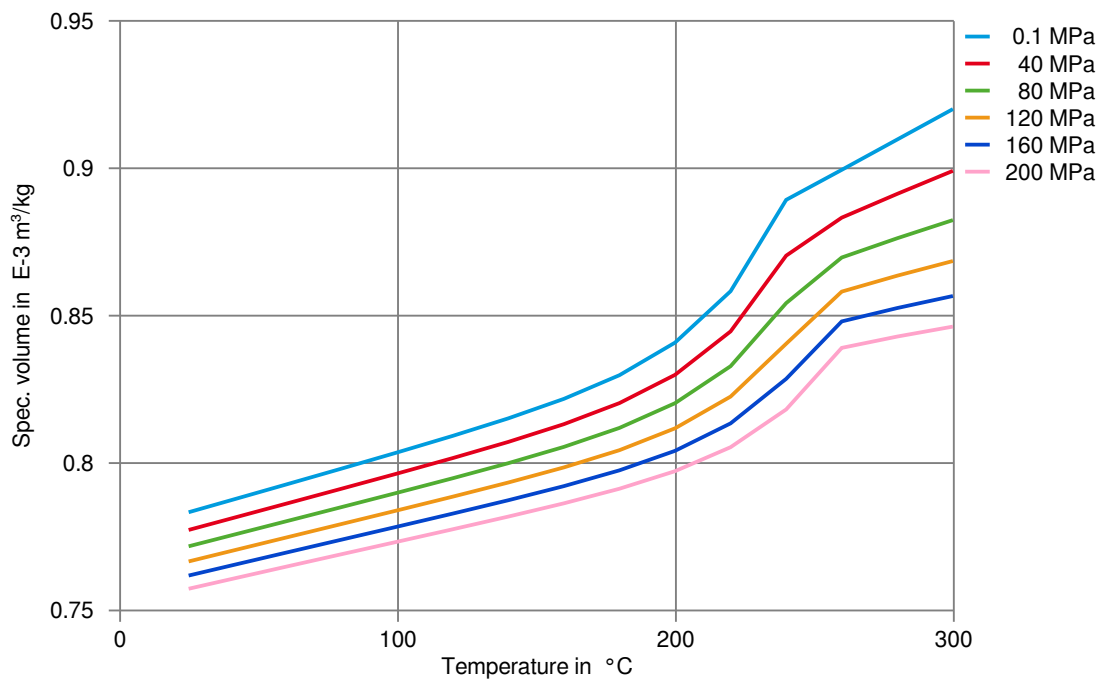

# Zytel® BM73G15THS BK317

NYLON RESIN


Tensile modulus-temperature (dry)

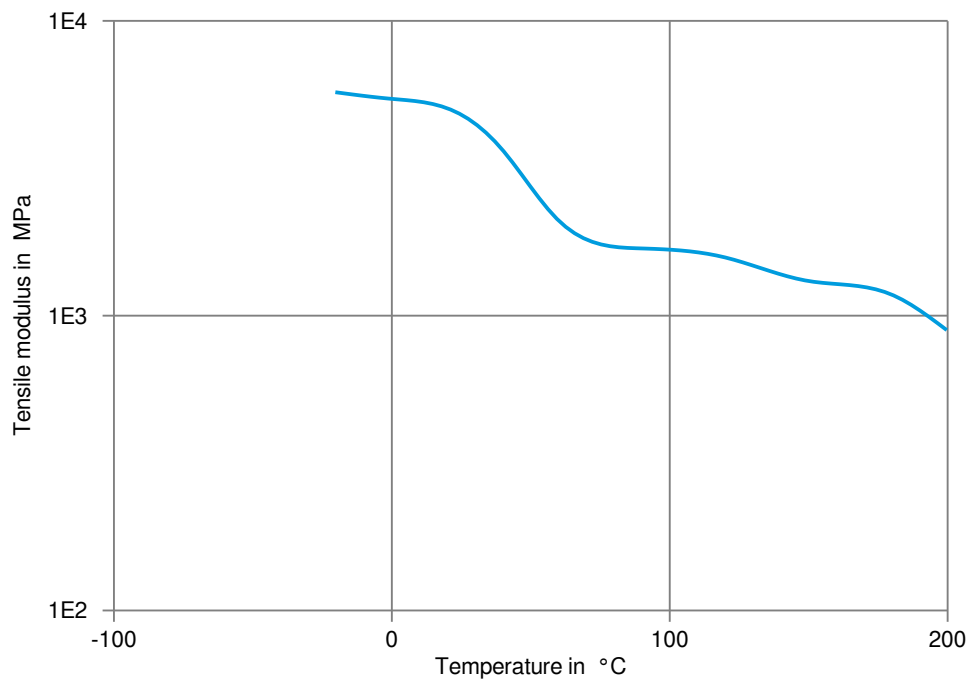

# Zytel® BM73G15THS BK317

NYLON RESIN

Tensile modulus-temperature (cond.)

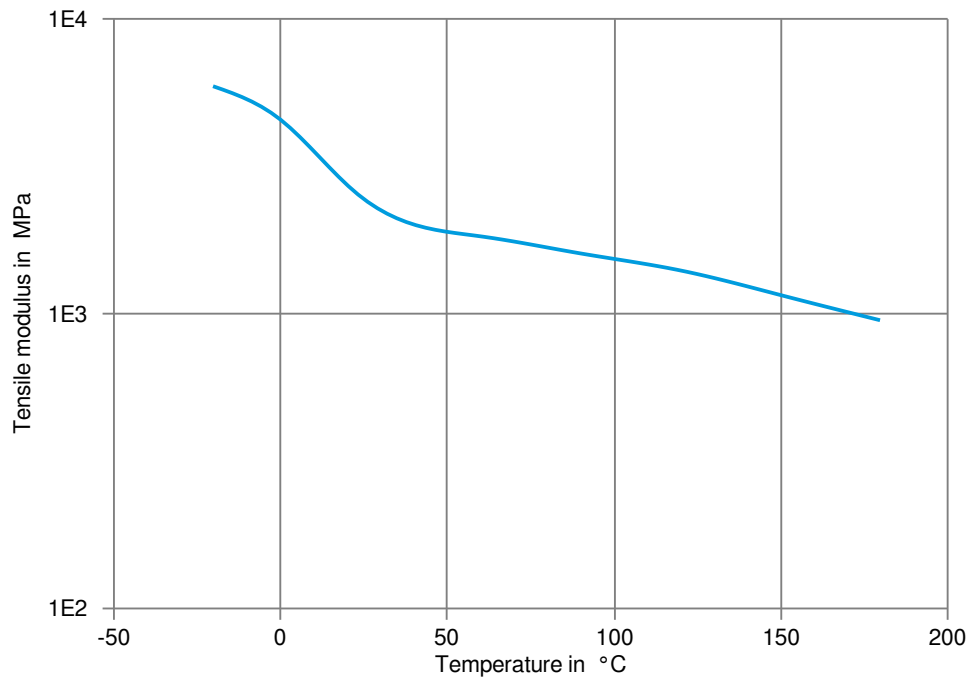

# Zytel® BM73G15THS BK317

## NYLON RESIN

### Chemical Media Resistance

#### Acids

- ✓ Acetic Acid (5% by mass), 23 °C
- ✓ Citric Acid solution (10% by mass), 23 °C
- ✓ Lactic Acid (10% by mass), 23 °C
- ✗ Hydrochloric Acid (36% by mass), 23 °C
- ✗ Nitric Acid (40% by mass), 23 °C
- ✗ Sulfuric Acid (38% by mass), 23 °C
- ✗ Sulfuric Acid (5% by mass), 23 °C
- ✗ Chromic Acid solution (40% by mass), 23 °C

#### Bases

- ✗ Sodium Hydroxide solution (35% by mass), 23 °C
- ✓ Sodium Hydroxide solution (1% by mass), 23 °C
- ✓ Ammonium Hydroxide solution (10% by mass), 23 °C

#### Alcohols

- ✓ Isopropyl alcohol, 23 °C
- ✓ Methanol, 23 °C
- ✓ Ethanol, 23 °C

#### Hydrocarbons

- ✓ n-Hexane, 23 °C
- ✓ Toluene, 23 °C
- ✓ iso-Octane, 23 °C

#### Ketones

- ✓ Acetone, 23 °C

#### Ethers

- ✓ Diethyl ether, 23 °C

#### Mineral oils

- ✓ SAE 10W40 multigrade motor oil, 23 °C
- ✓ SAE 10W40 multigrade motor oil, 130 °C
- ✓ SAE 80/90 hypoid-gear oil, 130 °C
- ✓ Insulating Oil, 23 °C
- ✓ Motor oil OS206 304 Ref.Eng.Oil, ISP, 135 °C

#### Standard Fuels

- ✓ ISO 1817 Liquid 1 - E5, 60 °C
- ✓ ISO 1817 Liquid 2 - M15E4, 60 °C
- ✓ ISO 1817 Liquid 3 - M3E7, 60 °C
- ✓ ISO 1817 Liquid 4 - M15, 60 °C
- ✓ Standard fuel without alcohol (pref. ISO 1817 Liquid C), 23 °C
- ✓ Standard fuel with alcohol (pref. ISO 1817 Liquid 4), 23 °C
- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 23 °C
- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 90 °C

# Zytel® BM73G15THS BK317

## NYLON RESIN

- ✓ Diesel fuel (pref. ISO 1817 Liquid F), >90°C

### Salt solutions

- ✓ Sodium Chloride solution (10% by mass), 23°C
- ✗ Sodium Hypochlorite solution (10% by mass), 23°C
- ✓ Sodium Carbonate solution (20% by mass), 23°C
- ✓ Sodium Carbonate solution (2% by mass), 23°C
- ✗ Zinc Chloride solution (50% by mass), 23°C

### Other

- ✓ Ethyl Acetate, 23°C
- ✗ Hydrogen peroxide, 23°C
- ✓ DOT No. 4 Brake fluid, 130°C
- ✗ Ethylene Glycol (50% by mass) in water, 108°C
- ✓ 1% nonylphenoxy-polyethyleneoxy ethanol in water, 23°C
- ✓ 50% Oleic acid + 50% Olive Oil, 23°C
- ✓ Water, 23°C
- ✗ Water, 90°C
- ✗ Phenol solution (5% by mass), 23°C

### Symbols used:

- ✓ possibly resistant  
Defined as: Supplier has sufficient indication that contact with chemical can be potentially accepted under the intended use conditions and expected service life. Criteria for assessment have to be indicated (e.g. surface aspect, volume change, property change).
- ✗ not recommended - see explanation  
Defined as: Not recommended for general use. However, short-term exposure under certain restricted conditions could be acceptable (e.g. fast cleaning with thorough rinsing, spills, wiping, vapor exposure).