

# Zytel® 132F NC010

## NYLON RESIN

Common features of Zytel® nylon resin include mechanical and physical properties such as high mechanical strength, excellent balance of stiffness and toughness, good high temperature performance, good electrical and flammability properties, good abrasion and chemical resistance. In addition, Zytel® nylon resins are available in different modified and reinforced grades to create a wide range of products with tailored properties for specific processes and end-uses. Zytel® nylon resin, including most flame retardant grades, offer the ability to be coloured.

The good melt stability of Zytel® nylon resin normally enables the recycling of properly handled production waste. If recycling is not possible, we recommend, as the preferred option, incineration with energy recovery (-31kJ/g of base polymer) in appropriately equipped installations. For disposal, local regulations have to be observed.

Zytel® nylon resin typically is used in demanding applications in the automotive, furniture, domestic appliances, sporting goods and construction industry.

Zytel® 132F NC010 is a nucleated, lubricated polyamide 66 for injection moulding. It was developed for fast production cycles and high productivity applications.

### Product information

Resin Identification	PA66	ISO 1043
Part Marking Code	>PA66<	ISO 11469
ISO designation	ISO 16396-PA66,,M1G1NR,S14-030	

### Rheological properties

	dry/cond.		
Viscosity number	143 / *	cm <sup>3</sup> /g	ISO 307, 1628
Moulding shrinkage, parallel	0.9 / -	%	ISO 294-4, 2577
Moulding shrinkage, normal	1.2 / -	%	ISO 294-4, 2577

### Typical mechanical properties

	dry/cond.		
Tensile modulus	3400 / 1600	MPa	ISO 527-1/-2
Tensile stress at yield, 50mm/min	91 / 60	MPa	ISO 527-1/-2
Tensile strain at yield, 50mm/min	4.5 / 22	%	ISO 527-1/-2
Nominal strain at break	13 / >50	%	ISO 527-1/-2
Tensile strain at break, 50mm/min	20 / -	%	ISO 527-1/-2
Flexural modulus	3000 / 1400	MPa	ISO 178
Flexural stress at 3.5%	100 / -	MPa	ISO 178
Charpy impact strength, 23°C	300 / N	kJ/m <sup>2</sup>	ISO 179/1eU
Charpy impact strength, -30°C	200 / -	kJ/m <sup>2</sup>	ISO 179/1eU
Charpy notched impact strength, 23°C	4 / 8	kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength, -30°C	3.5 / 2.5	kJ/m <sup>2</sup>	ISO 179/1eA
Izod notched impact strength, 23°C	4 / 8	kJ/m <sup>2</sup>	ISO 180/1A
Izod notched impact strength, -30°C	4.0 / 2.0	kJ/m <sup>2</sup>	ISO 180/1A
Izod impact strength, 23°C	300 / N	kJ/m <sup>2</sup>	ISO 180/1U
Poisson's ratio	0.37 / 0.42		

### Thermal properties

	dry/cond.		
Melting temperature, 10°C/min	262 / *	°C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	60 / 40	°C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	75 / *	°C	ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	225 / *	°C	ISO 75-1/-2

# Zytel® 132F NC010

## NYLON RESIN

RTI, electrical, 0.75mm	130	°C	UL 746B
RTI, electrical, 1.5mm	130	°C	UL 746B
RTI, electrical, 3.0mm	130	°C	UL 746B
RTI, electrical, 6mm	130	°C	UL 746B
RTI, impact, 0.75mm	75	°C	UL 746B
RTI, impact, 1.5mm	75	°C	UL 746B
RTI, impact, 3.0mm	75	°C	UL 746B
RTI, impact, 6mm	75	°C	UL 746B
RTI, strength, 0.75mm	85	°C	UL 746B
RTI, strength, 1.5mm	85/*	°C	UL 746B
RTI, strength, 3.0mm	85	°C	UL 746B
RTI, strength, 6mm	85	°C	UL 746B

### Flammability

	dry/cond.		
Burning Behav. at 1.5mm nom. thickn.	V-2/*	class	IEC 60695-11-10
Thickness tested	1.5/*	mm	IEC 60695-11-10
UL recognition	yes/*		UL 94
Burning Behav. at thickness h	V-2/*	class	IEC 60695-11-10
Thickness tested	0.71/*	mm	IEC 60695-11-10
UL recognition	yes/*		UL 94
Oxygen index	29/*	%	ISO 4589-1/-2
Glow Wire Flammability Index, 0.75mm	960/-	°C	IEC 60695-2-12
Glow Wire Flammability Index, 1.5mm	960/-	°C	IEC 60695-2-12
Glow Wire Flammability Index, 3.0mm	960/-	°C	IEC 60695-2-12
Glow Wire Ignition Temperature, 0.75mm	725/-	°C	IEC 60695-2-13
Glow Wire Ignition Temperature, 1.5mm	750/-	°C	IEC 60695-2-13
Glow Wire Ignition Temperature, 3.0mm	800/-	°C	IEC 60695-2-13
FMVSS Class	DNI		ISO 3795 (FMVSS 302)

### Physical/Other properties

	dry/cond.		
Humidity absorption, 2mm	2.6/*	%	Sim. to ISO 62
Water absorption, 2mm	8.5/*	%	Sim. to ISO 62
Density	1140/-	kg/m <sup>3</sup>	ISO 1183

### Film Properties

	dry/cond.		
Strain at yield, parallel	4.4/*	%	ISO 527-3

### Injection

Drying Recommended	yes
Drying Temperature	80 °C
Drying Time, Dehumidified Dryer	2 - 4 h
Processing Moisture Content	≤0.2 %
Melt Temperature Optimum	295 °C
Min. melt temperature	285 °C
Max. melt temperature	305 °C
Screw tangential speed	≤0.3 m/s
Mold Temperature Optimum	70 °C
Min. mould temperature	40 °C

# Zytel® 132F NC010


## NYLON RESIN

Max. mould temperature	95 °C
Hold pressure range	50 - 100 MPa
Hold pressure time	4 s/mm
Ejection temperature	225 °C

### Characteristics

Processing	Injection Moulding
Delivery form	Pellets
Additives	Release agent


### Stress-strain (dry)

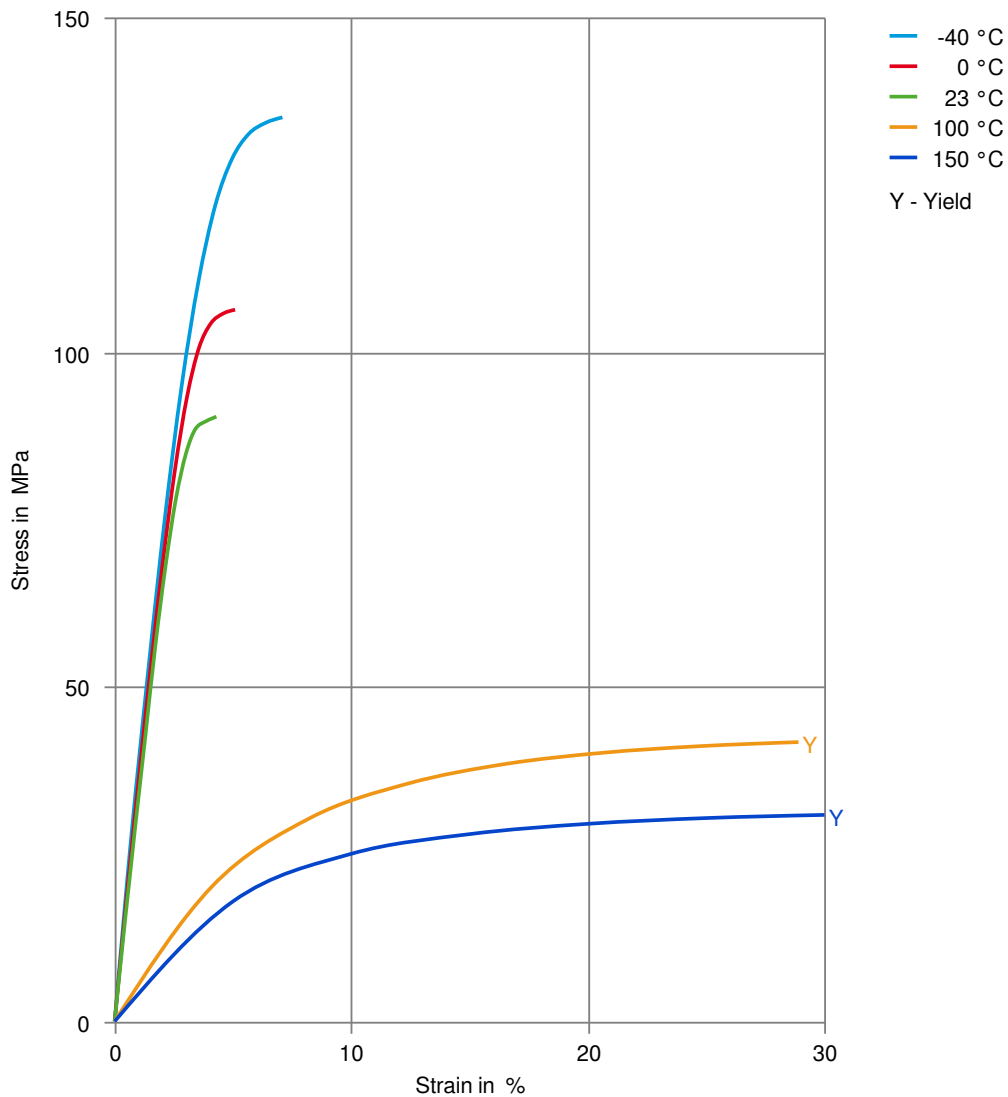

# Zytel® 132F NC010

NYLON RESIN

Secant modulus-strain (dry)

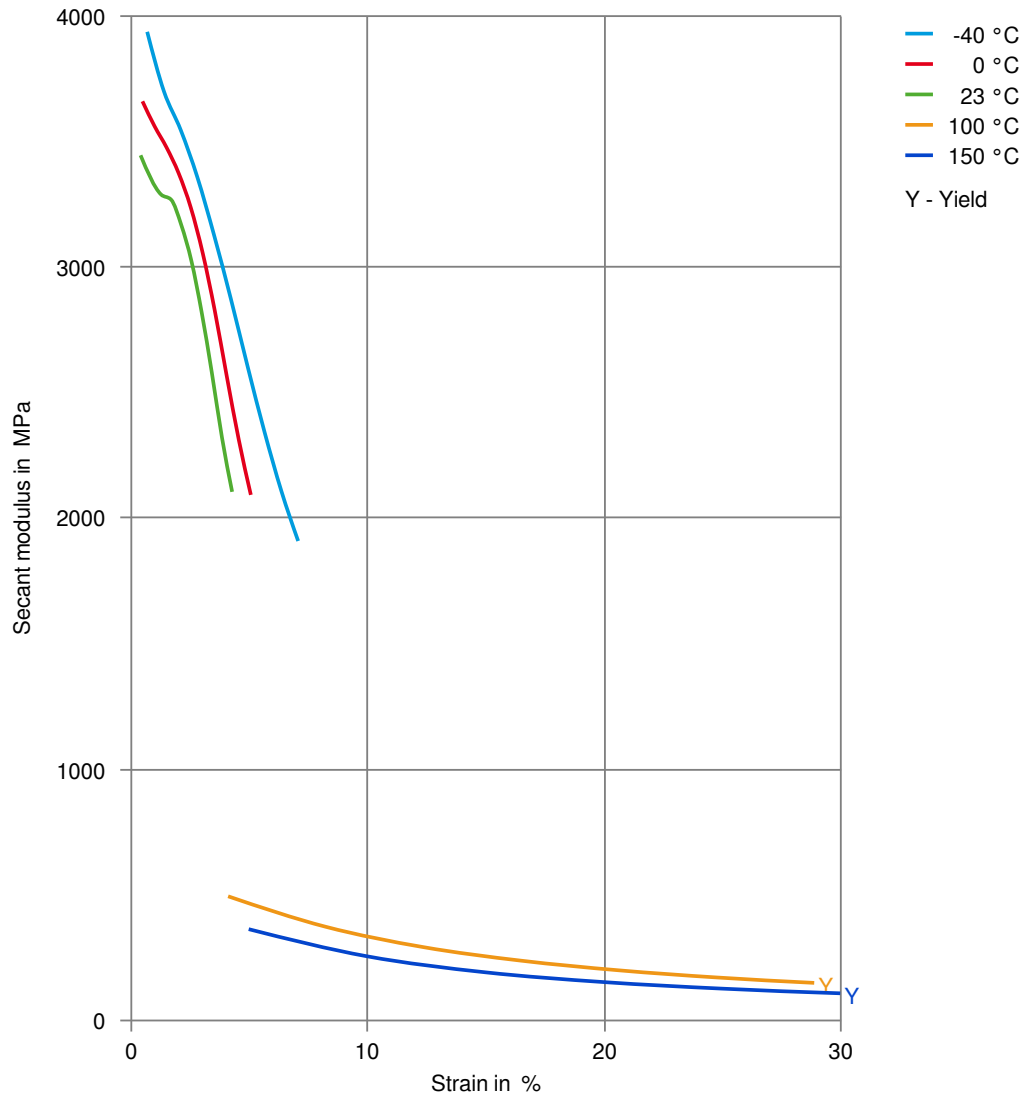

# Zytel® 132F NC010

## NYLON RESIN

### Chemical Media Resistance

#### Acids

- ✓ Acetic Acid (5% by mass), 23°C
- ✓ Citric Acid solution (10% by mass), 23°C
- ✓ Lactic Acid (10% by mass), 23°C
- ✗ Hydrochloric Acid (36% by mass), 23°C
- ✗ Nitric Acid (40% by mass), 23°C
- ✗ Sulfuric Acid (38% by mass), 23°C
- ✗ Sulfuric Acid (5% by mass), 23°C
- ✗ Chromic Acid solution (40% by mass), 23°C

#### Bases

- ✗ Sodium Hydroxide solution (35% by mass), 23°C
- ✓ Sodium Hydroxide solution (1% by mass), 23°C
- ✓ Ammonium Hydroxide solution (10% by mass), 23°C

#### Alcohols

- ✓ Isopropyl alcohol, 23°C
- ✓ Methanol, 23°C
- ✓ Ethanol, 23°C

#### Hydrocarbons

- ✓ n-Hexane, 23°C
- ✓ Toluene, 23°C
- ✓ iso-Octane, 23°C

#### Ketones

- ✓ Acetone, 23°C

#### Ethers

- ✓ Diethyl ether, 23°C

#### Mineral oils

- ✓ SAE 10W40 multigrade motor oil, 23°C
- ✗ SAE 10W40 multigrade motor oil, 130°C
- ✗ SAE 80/90 hypoid-gear oil, 130°C
- ✓ Insulating Oil, 23°C

#### Standard Fuels

- ✓ ISO 1817 Liquid 1 - E5, 60°C
- ✓ ISO 1817 Liquid 2 - M15E4, 60°C
- ✓ ISO 1817 Liquid 3 - M3E7, 60°C
- ✓ ISO 1817 Liquid 4 - M15, 60°C
- ✓ Standard fuel without alcohol (pref. ISO 1817 Liquid C), 23°C
- ✓ Standard fuel with alcohol (pref. ISO 1817 Liquid 4), 23°C
- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 23°C
- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 90°C
- ✗ Diesel fuel (pref. ISO 1817 Liquid F), >90°C

#### Salt solutions

- ✓ Sodium Chloride solution (10% by mass), 23°C
- ✗ Sodium Hypochlorite solution (10% by mass), 23°C

# Zytel® 132F NC010

## NYLON RESIN

- ✓ Sodium Carbonate solution (20% by mass), 23 °C
- ✓ Sodium Carbonate solution (2% by mass), 23 °C
- ✗ Zinc Chloride solution (50% by mass), 23 °C

### Other

- ✓ Ethyl Acetate, 23 °C
- ✗ Hydrogen peroxide, 23 °C
- ✗ DOT No. 4 Brake fluid, 130 °C
- ✗ Ethylene Glycol (50% by mass) in water, 108 °C
- ✓ 1% nonylphenoxy-polyethyleneoxy ethanol in water, 23 °C
- ✓ 50% Oleic acid + 50% Olive Oil, 23 °C
- ✓ Water, 23 °C
- ✗ Water, 90 °C
- ✗ Phenol solution (5% by mass), 23 °C

### Symbols used:

- ✓ possibly resistant  
Defined as: Supplier has sufficient indication that contact with chemical can be potentially accepted under the intended use conditions and expected service life. Criteria for assessment have to be indicated (e.g. surface aspect, volume change, property change).
- ✗ not recommended - see explanation  
Defined as: Not recommended for general use. However, short-term exposure under certain restricted conditions could be acceptable (e.g. fast cleaning with thorough rinsing, spills, wiping, vapor exposure).