

# Zytel® ST801AHS BK010

## NYLON RESIN

Common features of Zytel® nylon resin include mechanical and physical properties such as high mechanical strength, excellent balance of stiffness and toughness, good high temperature performance, good electrical and flammability properties, good abrasion and chemical resistance. In addition, Zytel® nylon resins are available in different modified and reinforced grades to create a wide range of products with tailored properties for specific processes and end-uses. Zytel® nylon resin, including most flame retardant grades, offer the ability to be coloured.

The good melt stability of Zytel® nylon resin normally enables the recycling of properly handled production waste. If recycling is not possible, we recommend, as the preferred option, incineration with energy recovery (-31kJ/g of base polymer) in appropriately equipped installations. For disposal, local regulations have to be observed.

Zytel® nylon resin typically is used in demanding applications in the automotive, furniture, domestic appliances, sporting goods and construction industry.

Zytel® ST801AHS BK010 is a Super Tough, high performance polyamide 66 resin. It offers outstanding moulding performance in injection molding applications.

### Product information

Resin Identification	PA66-HI	ISO 1043
Part Marking Code	>PA66-HI<	ISO 11469
ISO designation	ISO 16396-PA66-I,,M1CG1HR,S12-020	

### Rheological properties

	dry/cond.		
Melt mass-flow rate	19 / *	g/10min	ISO 1133
Melt mass-flow rate, Temperature	275 / *	°C	
Melt mass-flow rate, Load	5 / *	kg	
Viscosity number	120 / *	cm <sup>3</sup> /g	ISO 307, 1628
Moulding shrinkage, parallel	1.8 / -	%	ISO 294-4, 2577
Moulding shrinkage, normal	1.4 / -	%	ISO 294-4, 2577

### Typical mechanical properties

	dry/cond.		
Tensile modulus	2000 / 1100	MPa	ISO 527-1/-2
Tensile stress at yield, 50mm/min	50 / 39	MPa	ISO 527-1/-2
Tensile strain at yield, 50mm/min	4 / 39	%	ISO 527-1/-2
Nominal strain at break	50 / >50	%	ISO 527-1/-2
Tensile strain at break, 50mm/min	50 / -	%	ISO 527-1/-2
Flexural modulus	1900 / 800	MPa	ISO 178
Charpy impact strength, 23°C	N / N	kJ/m <sup>2</sup>	ISO 179/1eU
Charpy notched impact strength, 23°C	75 / 105	kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength, -30°C	17 / 15	kJ/m <sup>2</sup>	ISO 179/1eA
Izod notched impact strength, 23°C	70 / -	kJ/m <sup>2</sup>	ISO 180/1A
Izod notched impact strength, -30°C	19.0 / -	kJ/m <sup>2</sup>	ISO 180/1A
Izod notched impact strength, -40°C	17.0 / -	kJ/m <sup>2</sup>	ISO 180/1A
Izod impact strength, 23°C	N / -	kJ/m <sup>2</sup>	ISO 180/1U
Hardness, Rockwell, R-scale	107 / 69		ISO 2039-2
Poisson's ratio	0.4 / 0.45		

# Zytel® ST801AHS BK010

## NYLON RESIN

### Thermal properties

	dry/cond.			
Melting temperature, 10°C/min	262 / *	°C		ISO 11357-1/-3
Glass transition temperature, 10°C/min	75 / 20	°C		ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	61 / *	°C		ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	147 / *	°C		ISO 75-1/-2
Coefficient of linear thermal expansion (CLTE), parallel	140 / *	E-6/K		ISO 11359-1/-2
Coefficient of linear thermal expansion (CLTE), normal	120 / *	E-6/K		ISO 11359-1/-2
RTI, electrical, 0.75mm	130	°C		UL 746B
RTI, electrical, 1.5mm	130	°C		UL 746B
RTI, electrical, 3.0mm	130	°C		UL 746B
RTI, impact, 0.75mm	65	°C		UL 746B
RTI, impact, 1.5mm	105	°C		UL 746B
RTI, impact, 3.0mm	105	°C		UL 746B
RTI, strength, 0.75mm	95	°C		UL 746B
RTI, strength, 1.5mm	105 / *	°C		UL 746B
RTI, strength, 3.0mm	110	°C		UL 746B

### Flammability

	dry/cond.			
Burning Behav. at 1.5mm nom. thickn.	HB / *	class		IEC 60695-11-10
Thickness tested	1.5 / *	mm		IEC 60695-11-10
UL recognition	yes / *			UL 94
Burning Behav. at thickness h	HB / *	class		IEC 60695-11-10
Thickness tested	0.75 / *	mm		IEC 60695-11-10
UL recognition	yes / *			UL 94
FMVSS Class	B			ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	26	mm/min		ISO 3795 (FMVSS 302)

### Electrical properties

	dry/cond.			
Electric strength	24 / - <sup>[DS]</sup>	kV/mm		IEC 60243-1
Comparative tracking index	600 / - <sup>[DS]</sup>			IEC 60112

[DS]: Derived from similar grade

### Physical/Other properties

	dry/cond.			
Humidity absorption, 2mm	2 / *	%		Sim. to ISO 62
Water absorption, 2mm	6.5 / *	%		Sim. to ISO 62
Water absorption, Immersion 24h	1.1 <sup>[1]</sup> / *	%		Sim. to ISO 62
Density	1080 / -	kg/m <sup>3</sup>		ISO 1183

[1]: 3mm wall thickness

### VDA Properties

	dry/cond.			
Emission of organic compounds	13	µgC/g		VDA 277
Odour	5	class		VDA 270
Fogging, G-value (condensate)	0.1 / *	mg		ISO 6452

# Zytel® ST801AHS BK010

## NYLON RESIN

### Injection

Drying Recommended	yes
Drying Temperature	80 °C
Drying Time, Dehumidified Dryer	2 - 4 h
Processing Moisture Content	≤0.2 %
Melt Temperature Optimum	285 °C
Min. melt temperature	270 °C
Max. melt temperature	300 °C
Screw tangential speed	≤0.3 m/s
Mold Temperature Optimum	70 °C
Min. mould temperature	50 °C
Max. mould temperature	90 °C
Hold pressure range	50 - 100 MPa
Hold pressure time	4 s/mm
Ejection temperature	216 °C

### Extrusion

Drying Temperature	≤80 °C
Drying Time, Dehumidified Dryer	3 - 4 h
Processing Moisture Content	≤0.06 %
Melt Temperature Optimum	280 °C
Melt Temperature Range	275 - 290 °C

### Characteristics

Processing	Injection Moulding
Special characteristics	High impact or impact modified, Heat stabilised or stable to heat


### Automotive

OEM	STANDARD	ADDITIONAL INFORMATION
Ford	WSS-M4D666-B1	
General Motors	GMW16447P-PA66-T3	Black
Hyundai	MS211-46 Type C-2	
Mercedes-Benz	DBL5403.22 PA66-I	
Mercedes-Benz	DBL5410.01 PA66-I	
Renault-Nissan	UB15b, No Spec, Special Part Approval, See Your CE Account Manager.	
Stellantis	MS.50017 / PA66.1800F.70I.HS.TG	CPN2565
Stellantis - Chrysler	MS.50017 / CPN-2565	Black
VW Group	VW 50127 PA66-2	
VW Group	VW 50127 PA66-3	
VW Group	VW 50133 PA66-2-A	

# Zytel® ST801AHS BK010

NYLON RESIN


Stress-strain (dry)

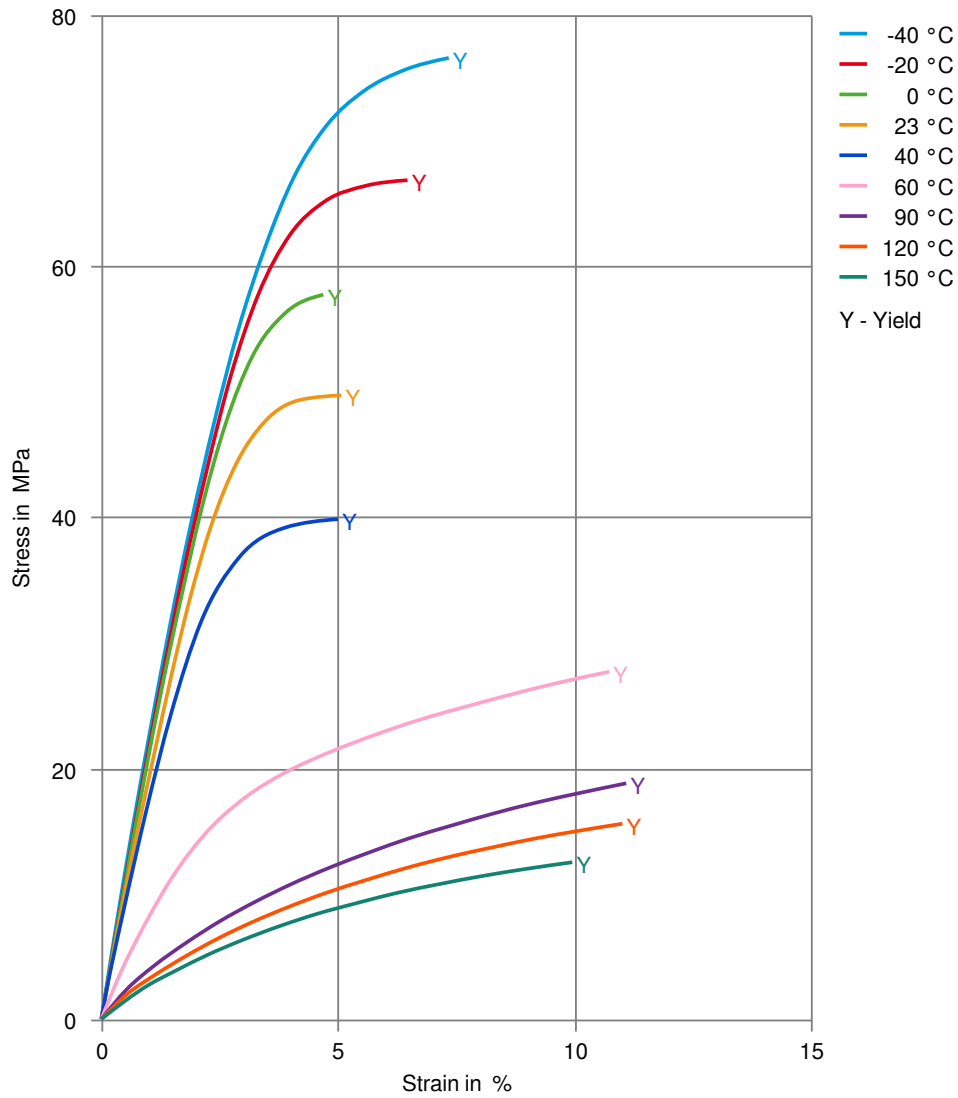

# Zytel® ST801AHS BK010

NYLON RESIN


Stress-strain (cond.)

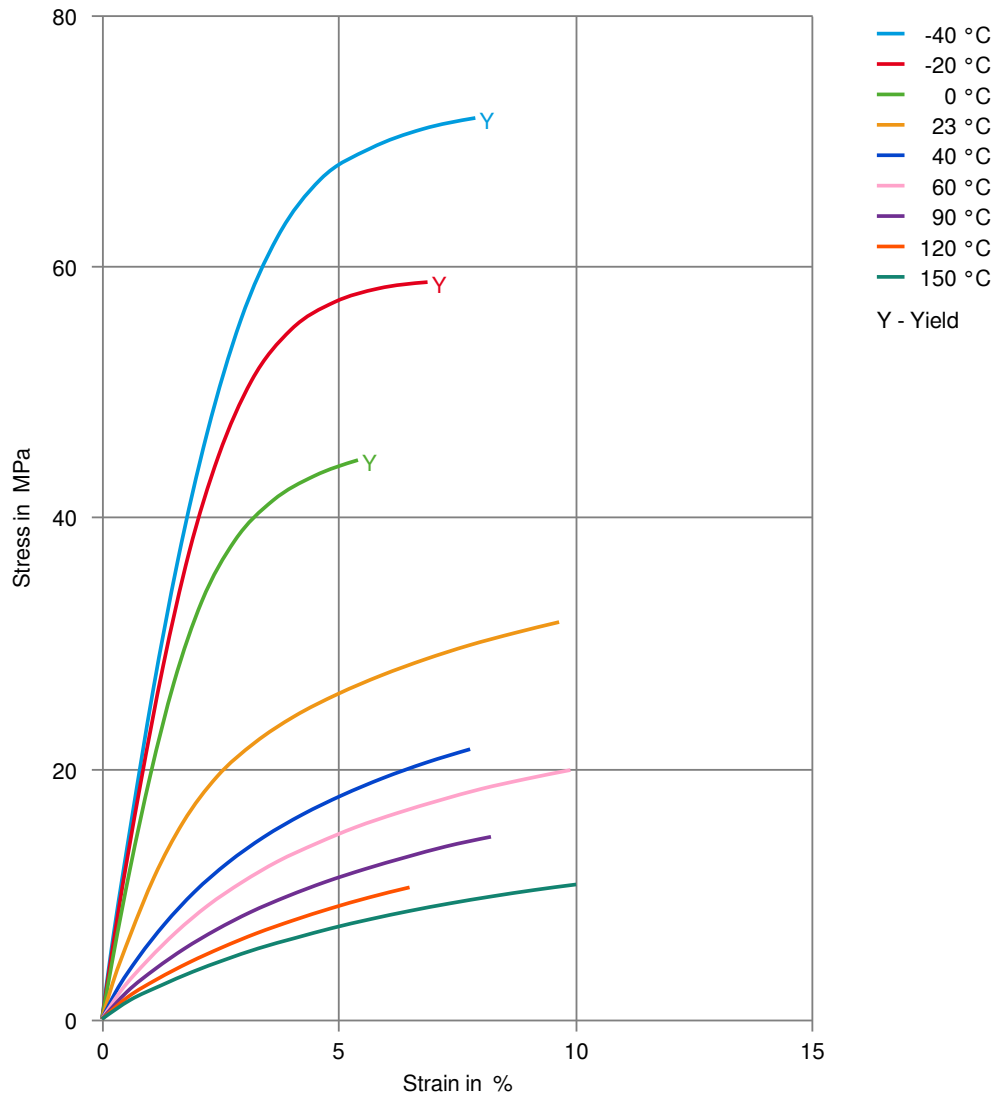

# Zytel® ST801AHS BK010

NYLON RESIN


Secant modulus-strain (dry)

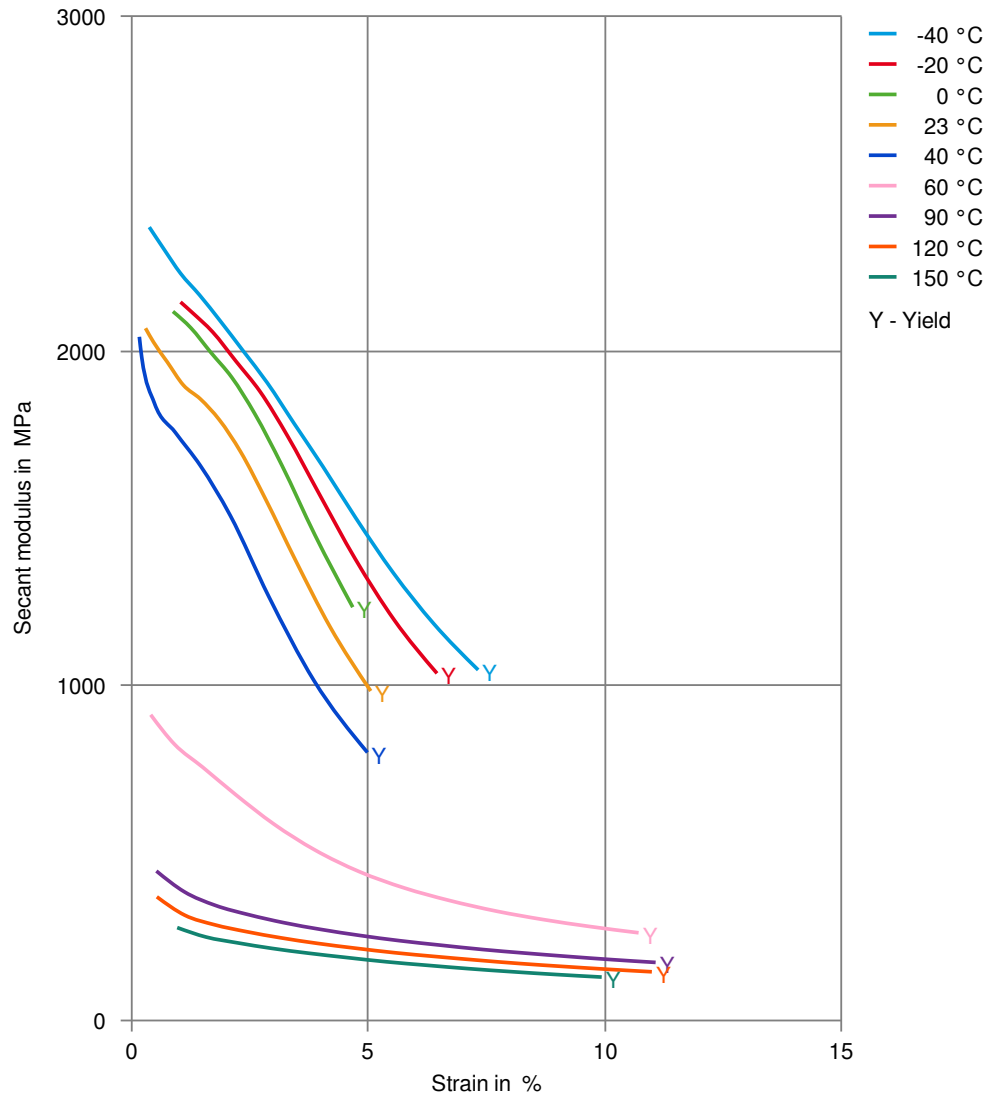

# Zytel® ST801AHS BK010

NYLON RESIN

Secant modulus-strain (cond.)

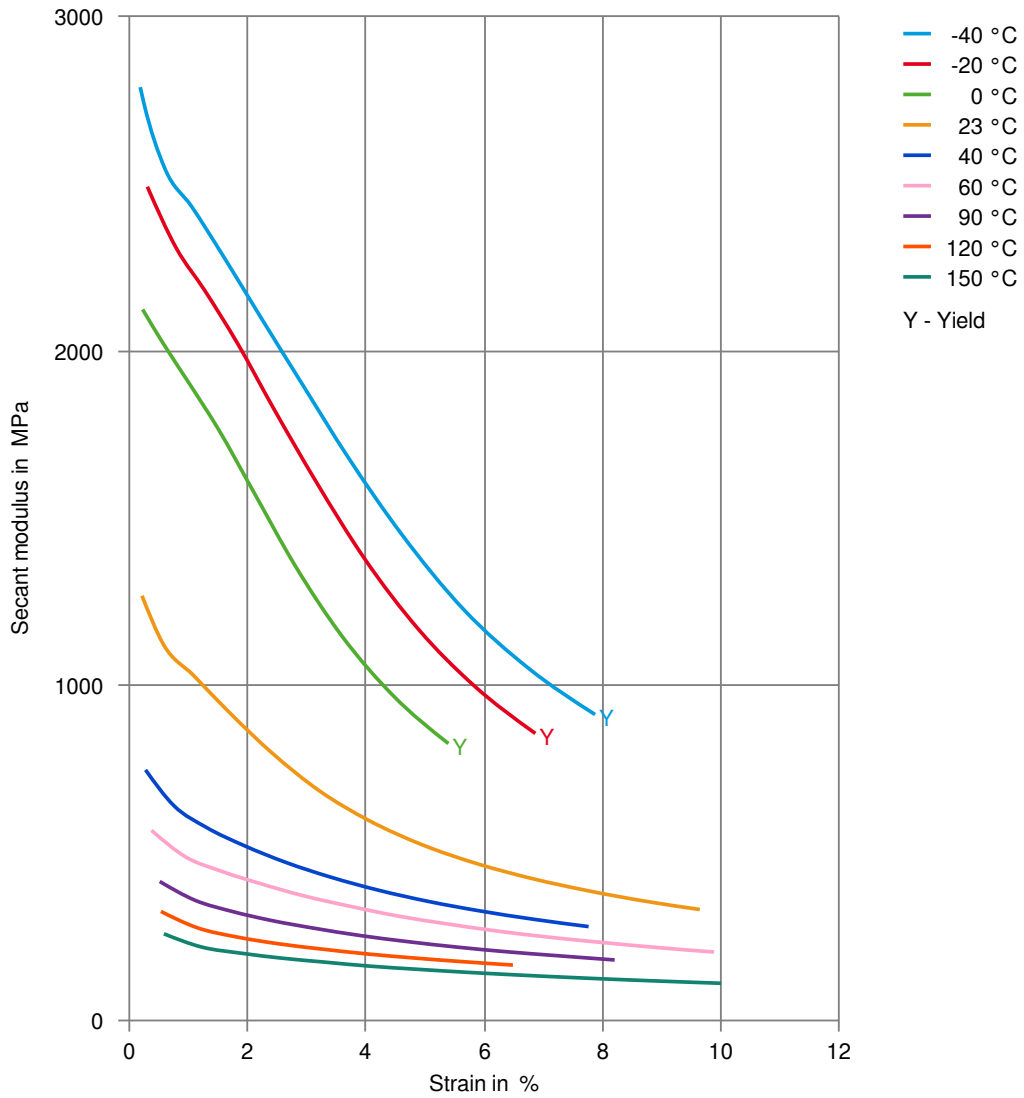

# Zytel® ST801AHS BK010

## NYLON RESIN

### Chemical Media Resistance

#### Acids

- ✓ Acetic Acid (5% by mass), 23°C
- ✓ Citric Acid solution (10% by mass), 23°C
- ✓ Lactic Acid (10% by mass), 23°C
- ✗ Hydrochloric Acid (36% by mass), 23°C
- ✗ Nitric Acid (40% by mass), 23°C
- ✗ Sulfuric Acid (38% by mass), 23°C
- ✗ Sulfuric Acid (5% by mass), 23°C
- ✗ Chromic Acid solution (40% by mass), 23°C

#### Bases

- ✗ Sodium Hydroxide solution (35% by mass), 23°C
- ✓ Sodium Hydroxide solution (1% by mass), 23°C
- ✓ Ammonium Hydroxide solution (10% by mass), 23°C

#### Alcohols

- ✓ Isopropyl alcohol, 23°C
- ✓ Methanol, 23°C
- ✓ Ethanol, 23°C

#### Hydrocarbons

- ✓ n-Hexane, 23°C
- ✓ Toluene, 23°C
- ✓ iso-Octane, 23°C

#### Ketones

- ✓ Acetone, 23°C

#### Ethers

- ✓ Diethyl ether, 23°C

#### Mineral oils

- ✓ SAE 10W40 multigrade motor oil, 23°C
- ✓ SAE 10W40 multigrade motor oil, 130°C
- ✓ SAE 80/90 hypoid-gear oil, 130°C
- ✓ Insulating Oil, 23°C
- ✓ Motor oil OS206 304 Ref.Eng.Oil, ISP, 135°C
- ✓ Automatic hypoid-gear oil Shell Donax TX, 135°C
- ✓ Hydraulic oil Pentosin CHF 202, 125°C

#### Standard Fuels

- ✓ ISO 1817 Liquid 1 - E5, 60°C
- ✓ ISO 1817 Liquid 2 - M15E4, 60°C
- ✓ ISO 1817 Liquid 3 - M3E7, 60°C
- ✓ ISO 1817 Liquid 4 - M15, 60°C
- ✓ Standard fuel without alcohol (pref. ISO 1817 Liquid C), 23°C
- ✓ Standard fuel with alcohol (pref. ISO 1817 Liquid 4), 23°C
- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 23°C
- ✗ Diesel fuel (pref. ISO 1817 Liquid F), 90°C
- ✗ Diesel fuel (pref. ISO 1817 Liquid F), >90°C

# Zytel® ST801AHS BK010

## NYLON RESIN

### Salt solutions

- ✓ Sodium Chloride solution (10% by mass), 23 °C
- ✗ Sodium Hypochlorite solution (10% by mass), 23 °C
- ✓ Sodium Carbonate solution (20% by mass), 23 °C
- ✓ Sodium Carbonate solution (2% by mass), 23 °C
- ✗ Zinc Chloride solution (50% by mass), 23 °C

### Other

- ✓ Ethyl Acetate, 23 °C
- ✗ Hydrogen peroxide, 23 °C
- ✗ DOT No. 4 Brake fluid, 130 °C
- ✗ Ethylene Glycol (50% by mass) in water, 108 °C
- ✓ 1% nonylphenoxy-polyethyleneoxy ethanol in water, 23 °C
- ✓ 50% Oleic acid + 50% Olive Oil, 23 °C
- ✓ Water, 23 °C
- ✓ Water, 90 °C
- ✗ Phenol solution (5% by mass), 23 °C

### Symbols used:

- ✓ possibly resistant  
Defined as: Supplier has sufficient indication that contact with chemical can be potentially accepted under the intended use conditions and expected service life. Criteria for assessment have to be indicated (e.g. surface aspect, volume change, property change).
- ✗ not recommended - see explanation  
Defined as: Not recommended for general use. However, short-term exposure under certain restricted conditions could be acceptable (e.g. fast cleaning with thorough rinsing, spills, wiping, vapor exposure).