

CELANEX® 2300 GV3/20

CELANEX® PBT

Chemical abbreviation according to ISO 1043-1: PBT Moulding compound ISO 7792- PBT, MGHR, 08-040N, GB20

Polybutylene terephthalate, low warpage, 20 % glass beads.

Flammability UL 94 HB minimum thickness 0.82 mm.

Recognition by Underwriters Laboratories, USA (UL)

Product information

Resin Identification	PBT-GB20	ISO 1043
Part Marking Code	>PBT-GB20<	ISO 11469

Rheological properties

Melt volume-flow rate	21 cm ³ /10min	ISO 1133
Temperature	250 °C	
Load	2.16 kg	
Moulding shrinkage range, parallel	1.6 - 2 %	ISO 294-4, 2577
Moulding shrinkage range, normal	1.4 - 1.7 %	ISO 294-4, 2577

Typical mechanical properties

Tensile modulus	3500 MPa	ISO 527-1/-2
Tensile stress at break, 5mm/min	52 MPa	ISO 527-1/-2
Tensile strain at break, 5mm/min	5 %	ISO 527-1/-2
Flexural strength	86 MPa	ISO 178
Flexural stress at 3.5%	85 MPa	ISO 178
Flexural strain at failure	4 %	ISO 178
Tensile creep modulus, 1h	3500 MPa	ISO 899-1
Tensile creep modulus, 1000h	2400 MPa	ISO 899-1
Charpy impact strength, 23°C	34 kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	34 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	3.5 kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	3.5 kJ/m ²	ISO 179/1eA
Ball indentation hardness, H 961/30	165 MPa	ISO 2039-1
Poisson's ratio	0.37 ^[C]	

[C]: Calculated

Thermal properties

Melting temperature, 10°C/min	225 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	70 °C	ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	180 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h 50N	190 °C	ISO 306
Coefficient of linear thermal expansion (CLTE), parallel	110 E-6/K	ISO 11359-1/-2

Flammability

Burning Behav. at 1.5mm nom. thickn.	HB class	IEC 60695-11-10
Thickness tested	1.6 mm	IEC 60695-11-10
Burning Behav. at thickness h	HB class	IEC 60695-11-10
Thickness tested	0.82 mm	IEC 60695-11-10
UL recognition	yes	UL 94
Oxygen index	21 %	ISO 4589-1/-2

CELANEX® 2300 GV3/20

CELANEX® PBT

Electrical properties

Relative permittivity, 100Hz	4.4	IEC 62631-2-1
Relative permittivity, 1MHz	4.2	IEC 62631-2-1
Dissipation factor, 100Hz	85 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	180 E-4	IEC 62631-2-1
Volume resistivity	>1E13 Ohm.m	IEC 62631-3-1
Surface resistivity	>1E15 Ohm	IEC 62631-3-2
Electric strength	26 kV/mm	IEC 60243-1
Comparative tracking index	225	IEC 60112

Physical/Other properties

Humidity absorption, 2mm	0.2 %	Sim. to ISO 62
Water absorption, 2mm	0.45 %	Sim. to ISO 62
Density	1450 kg/m ³	ISO 1183

VDA Properties

Odour	1.5 ^[1] class	VDA 270
-------	--------------------------	---------

[1]: Material test method was based on Odor per PV 3900 (19), Variant A3, not VDA 270

Injection

Drying Recommended	yes
Drying Temperature	120 °C
Drying Time, Dehumidified Dryer	4 h
Processing Moisture Content	≤0.02 %
Melt Temperature Optimum	250 °C
Min. melt temperature	240 °C
Max. melt temperature	260 °C
Screw tangential speed	0.1 - 0.3 m/s
Mold Temperature Optimum	80 °C
Min. mould temperature	60 °C
Max. mould temperature	130 °C

Characteristics

Processing	Injection Moulding
Delivery form	Pellets
Additives	Release agent
Special characteristics	Heat stabilised or stable to heat

Additional information

Injection molding

Preprocessing

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0,04%. The drying should be done in a dry-air dryer (dew point < -30 °C) with a temperature of 120 to 140 °C and a drying time of 2 to 4 hours. In case of longer residence times in the dry-air dryer, the temperature should be reduced to 100 °C.

CELANEX® 2300 GV3/20

CELANEX® PBT

The time between drying and processing should be kept as short as possible. The processing machine feed hopper should be closed during the processing operation.

Processing

Melt Temperature 240-260 °C
Mold Temperature *) 75-85 °C
Maximum Barrel Residence Time **) 5-10 min
Injection Speed fast
Peripheral screw speed max.0,3 m/sec
Back Pressure 10-30 bar
Injection Pressure 600-1000 bar
Holding Pressure 400-800 bar
Nozzle Design open design preferred

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided. For grades containing flame retardants, a maximum temperature of 265 °C should not be exceeded.

Celanese recommends only externally heated hot runner systems.

*) For moulded parts with especially high requirements to the surface quality or dimensional stability, a mold temperature of up to 110 °C can be advantageous.

**) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.

Processing Notes

Pre-Drying

CELANEX should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -30^{\circ}\text{C}$. The time between drying and processing should be as short as possible.

Storage

For subsequent storage of the material in the dryer until processed (≤ 60 h) it is necessary to lower the temperature to 100°C .

Automotive


OEM
Continental

STANDARD
SN 57908-17

CELANEX® 2300 GV3/20

CELANEX® PBT


Viscosity-shear rate

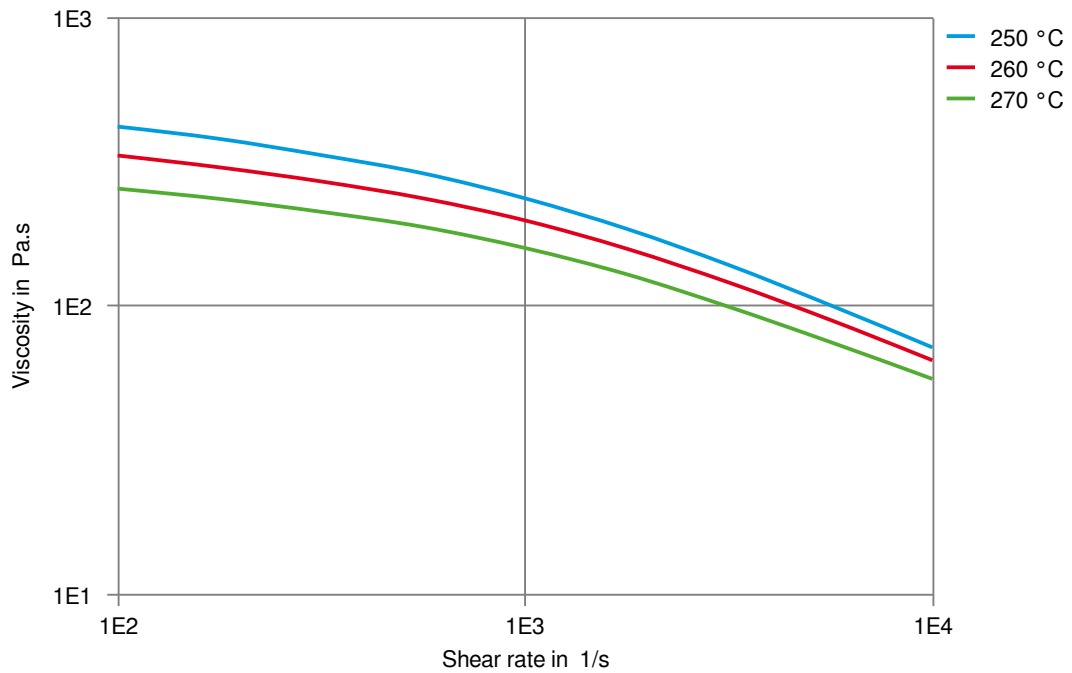

CELANEX® 2300 GV3/20

CELANEX® PBT


Shearstress-shear rate

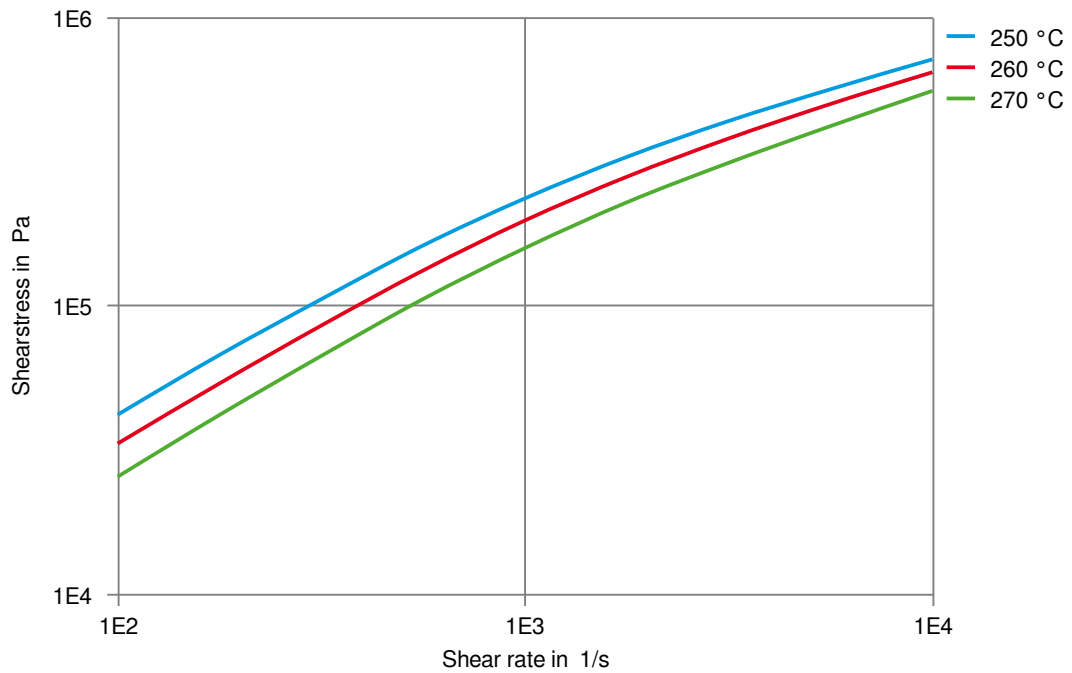

CELANEX® 2300 GV3/20

CELANEX® PBT

Stress-strain

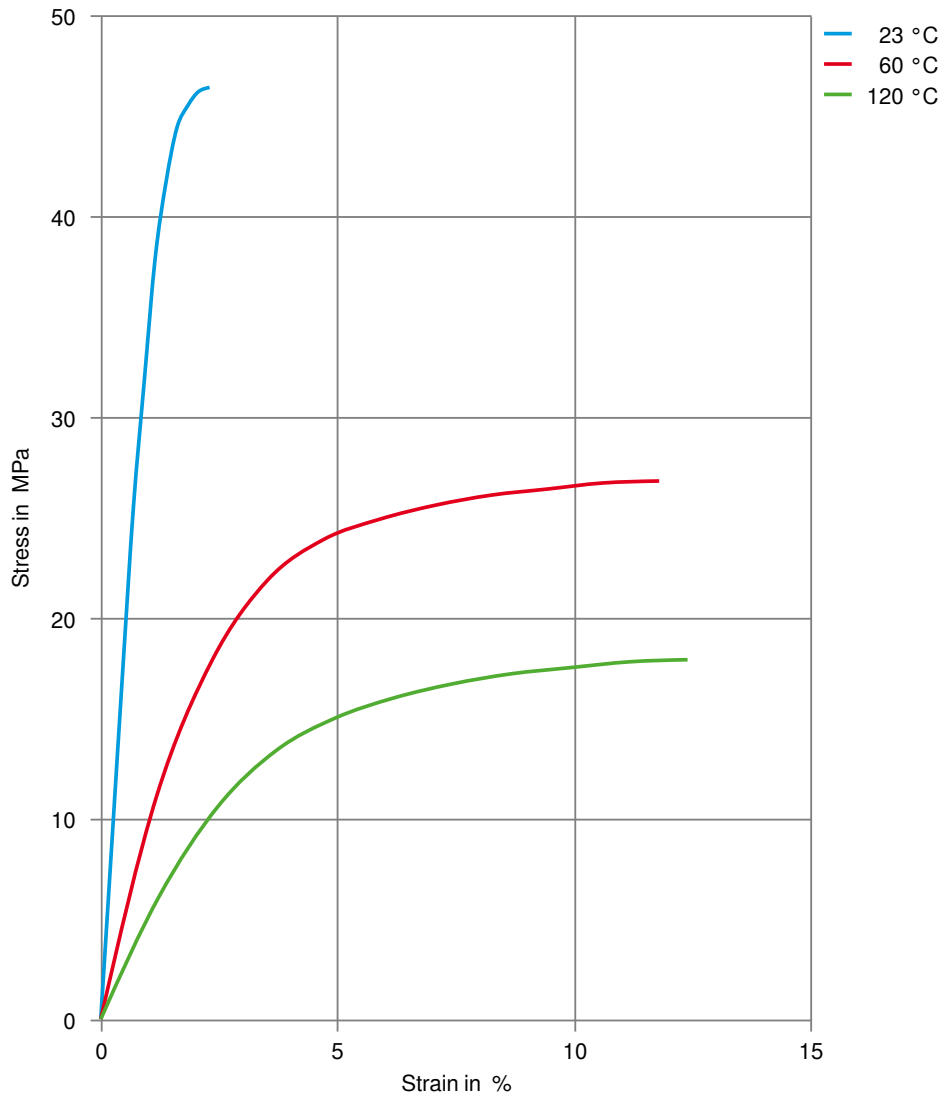

CELANEX® 2300 GV3/20

CELANEX® PBT

Secant modulus-strain

