

# CELANEX® 4016

## CELANEX® PBT

Non-exuding, unfilled, flame retardant polybutylene terephthalate which has an excellent balance of mechanical properties and processability. Celanex 4016 is well suited for applications requiring improved toughness.

### Product information

Resin Identification	PBT-I FR(17)	ISO 1043
Part Marking Code	>PBT-I FR(17)<	ISO 11469

### Rheological properties

Melt volume-flow rate	4.9 cm <sup>3</sup> /10min	ISO 1133
Temperature	250 °C	
Load	2.16 kg	
Melt mass-flow rate	5.5 g/10min	ISO 1133
Melt mass-flow rate, Temperature	250 °C	
Melt mass-flow rate, Load	2.16 kg	
Moulding shrinkage range, parallel	1.7 - 1.9 %	ISO 294-4, 2577
Moulding shrinkage range, normal	1.7 - 1.9 %	ISO 294-4, 2577

### Typical mechanical properties

Tensile modulus	2800 MPa	ISO 527-1/-2
Tensile stress at yield, 50mm/min	55 MPa	ISO 527-1/-2
Tensile strain at yield, 50mm/min	3.7 %	ISO 527-1/-2
Nominal strain at break	38 %	ISO 527-1/-2
Tensile strain at break, 50mm/min	38 %	ISO 527-1/-2
Flexural modulus	2630 MPa	ISO 178
Flexural strength	76 MPa	ISO 178
Charpy impact strength, 23°C	245 kJ/m <sup>2</sup>	ISO 179/1eU
Charpy impact strength, -30°C	105 kJ/m <sup>2</sup>	ISO 179/1eU
Charpy notched impact strength, 23°C	8.1 kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength, -30°C	8.1 kJ/m <sup>2</sup>	ISO 179/1eA
Izod notched impact strength, 23°C	7.7 kJ/m <sup>2</sup>	ISO 180/1A
Izod impact strength, 23°C	N kJ/m <sup>2</sup>	ISO 180/1U
Hardness, Rockwell, M-scale	60	ISO 2039-2
Poisson's ratio	0.37 <sup>[C]</sup>	
Shore D hardness, 15s	80	ISO 48-4 / ISO 868

[C]: Calculated

### Thermal properties

Melting temperature, 10°C/min	225 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	48 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	62 °C	ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	159 °C	ISO 75-1/-2
Coefficient of linear thermal expansion (CLTE), parallel	100 E-6/K	ISO 11359-1/-2
Coefficient of linear thermal expansion (CLTE), normal	100 E-6/K	ISO 11359-1/-2

# CELANEX® 4016

## CELANEX® PBT

### Flammability

Burning Behav. at thickness h	V-0 class	IEC 60695-11-10
Thickness tested	0.85 mm	IEC 60695-11-10
Oxygen index	30 %	ISO 4589-1/-2

### Electrical properties

Relative permittivity, 100Hz	3.1	IEC 62631-2-1
Relative permittivity, 1MHz	3.1	IEC 62631-2-1
Dissipation factor, 1MHz	200 E-4	IEC 62631-2-1
Volume resistivity	1E13 Ohm.m	IEC 62631-3-1
Surface resistivity	1E15 Ohm	IEC 62631-3-2
Electric strength	50 kV/mm	IEC 60243-1
Comparative tracking index	250	IEC 60112
Arc Resistance	80 s	UL 746B

### Physical/Other properties

Humidity absorption, 2mm	0.16 %	Sim. to ISO 62
Water absorption, 2mm	0.08 %	Sim. to ISO 62
Water absorption, Immersion 24h	0.08 %	Sim. to ISO 62
Density	1450 kg/m <sup>3</sup>	ISO 1183

### Injection

Drying Recommended	yes
Drying Temperature	120 °C
Drying Time, Dehumidified Dryer	4 h
Processing Moisture Content	≤0.02 %
Melt Temperature Optimum	250 °C
Min. melt temperature	240 °C
Max. melt temperature	260 °C
Screw tangential speed	0.1 - 0.3 m/s
Mold Temperature Optimum	80 °C
Min. mould temperature	60 °C
Max. mould temperature	130 °C
Ejection temperature	190 °C

### Characteristics

Processing	Injection Moulding
Delivery form	Pellets
Additives	Release agent, Flame retardant
Special characteristics	Flame retardant

### Additional information

Injection molding

### Preprocessing

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a

# CELANEX® 4016

CELANEX® PBT

dehumidifying hopper dryer capable of dewpoints <-30°F (-34 °C) at 250°F (121 °C) for 4 hours..

## Processing

Rear Temperature 450-470(230-240) deg F (deg C)  
Center Temperature 460-480(235-250) deg F (deg C)  
Front Temperature 470-490(240-255) deg F (deg C)  
Nozzle Temperature 480-490(250-255) deg F (deg C)  
Melt Temperature 460-490(235-255) deg F (deg C)  
Mold Temperature 150-200(65-93) deg F (deg C)  
Back Pressure 0-50 psi  
Screw Speed Medium  
Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 50% clean and dry regrind may be used for the '16 series' flame retardant grades.

Processing Notes

## Pre-Drying

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-40°F (-40 °C) at 250°F (121 °C) for 4 hours.

## Storage

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100° C.


## Automotive

OEM	STANDARD	ADDITIONAL INFORMATION
Li Auto	Q/LiA5310038	2021 (V2)
Stellantis - Chrysler	MS.50103 / CPN-3945	CPN3945, CPN3946
Stellantis - Chrysler	MS.50103 / CPN-3946	CPN3945, CPN3946

# CELANEX® 4016

CELANEX® PBT

## Stress-strain

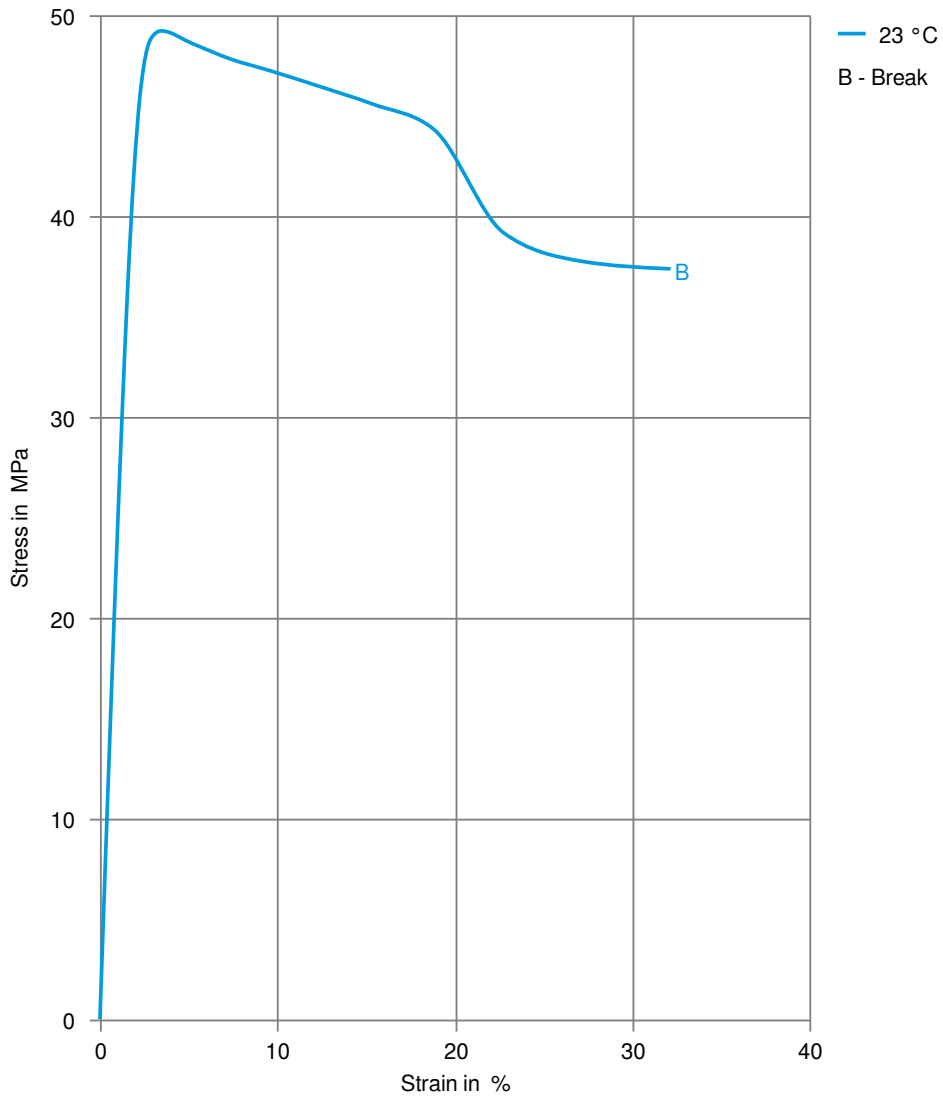

# CELANEX® 4016

CELANEX® PBT

## Secant modulus-strain

