

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN

Crastin® LW9020SF BK580 is a 20% glass fibre reinforced polybutylene terephthalate blend for

. It has improved surface aesthetics, excellent dimensional stability and low warpage characteristics.

Product information

Resin Identification	PBT+ASA-GF20	ISO 1043
Part Marking Code	>PBT+ASA-GF20<	ISO 11469

Rheological properties

Melt mass-flow rate	34 g/10min	ISO 1133
Melt mass-flow rate, Temperature	250 °C	
Melt mass-flow rate, Load	5 kg	
Moulding shrinkage, parallel	0.3 %	ISO 294-4, 2577
Moulding shrinkage, normal	0.8 %	ISO 294-4, 2577

Typical mechanical properties

Tensile Modulus	7000 MPa	ISO 527-1/-2
Stress at break, 5mm/min	110 MPa	ISO 527-1/-2
Strain at break, 5mm/min	2.5 %	ISO 527-1/-2
Charpy impact strength, 23°C	46 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	7 kJ/m ²	ISO 179/1eA
Poisson's ratio	0.35	

Thermal properties

Melting temperature, 10°C/min	224 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	120 °C	ISO 11357-1/-3
Temp. of deflection under load, 1.8 MPa	180 °C	ISO 75-1/-2
Temp. of deflection under load, 1.8 MPa, annealed	190 °C	ISO 75-1/-2
Thermal conductivity of melt	0.25 W/(m K)	Internal
Spec. heat capacity of melt	1850 J/(kg K)	Internal

Flammability

FMVSS Class	B	ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	<80 mm/min	ISO 3795 (FMVSS 302)

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN

Other properties

Density	1390 kg/m ³	ISO 1183
Density of melt	1210 kg/m ³	Internal


Injection

Drying Recommended	yes	
Drying Temperature	120 °C	
Drying Time, Dehumidified Dryer	2 - 4 h	
Processing Moisture Content	≤0.04 %	
Melt Temperature Optimum	250 °C	Internal
Min. melt temperature	240 °C	
Max. melt temperature	260 °C	
Mold Temperature Optimum	80 °C	
Min. mould temperature	30 °C	
Max. mould temperature	130 °C	
Hold pressure range	≥60 MPa	
Hold pressure time	3 s/mm	
Back pressure	As low as possible MPa	
Ejection temperature	170 °C	Internal

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN


Viscosity-shear rate

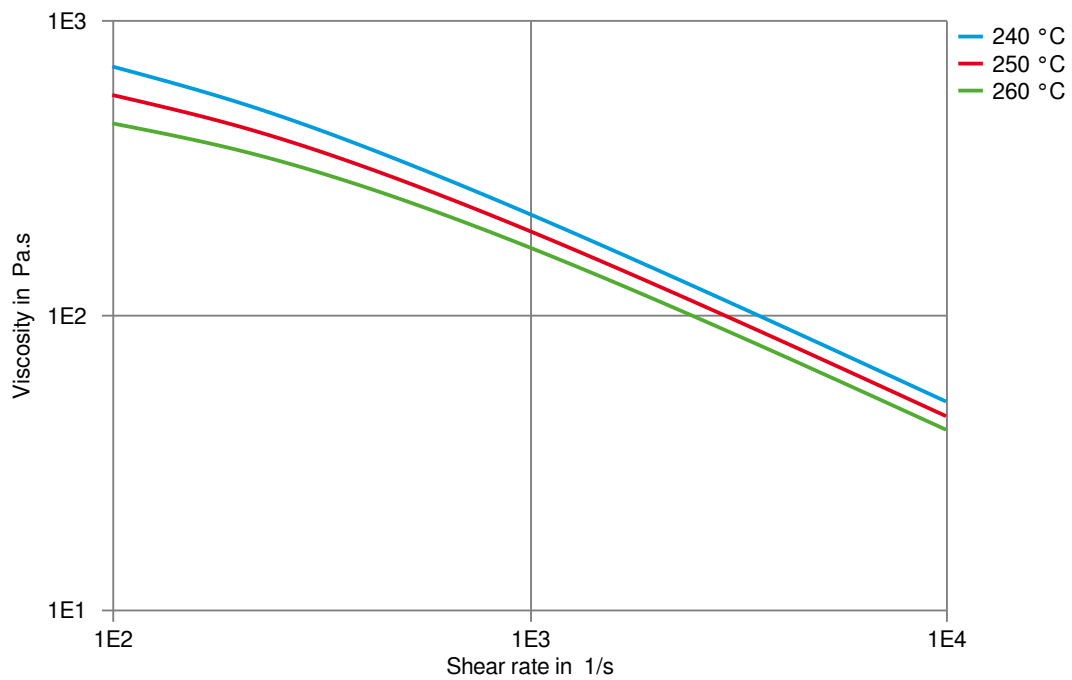

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN


Shearstress-shear rate

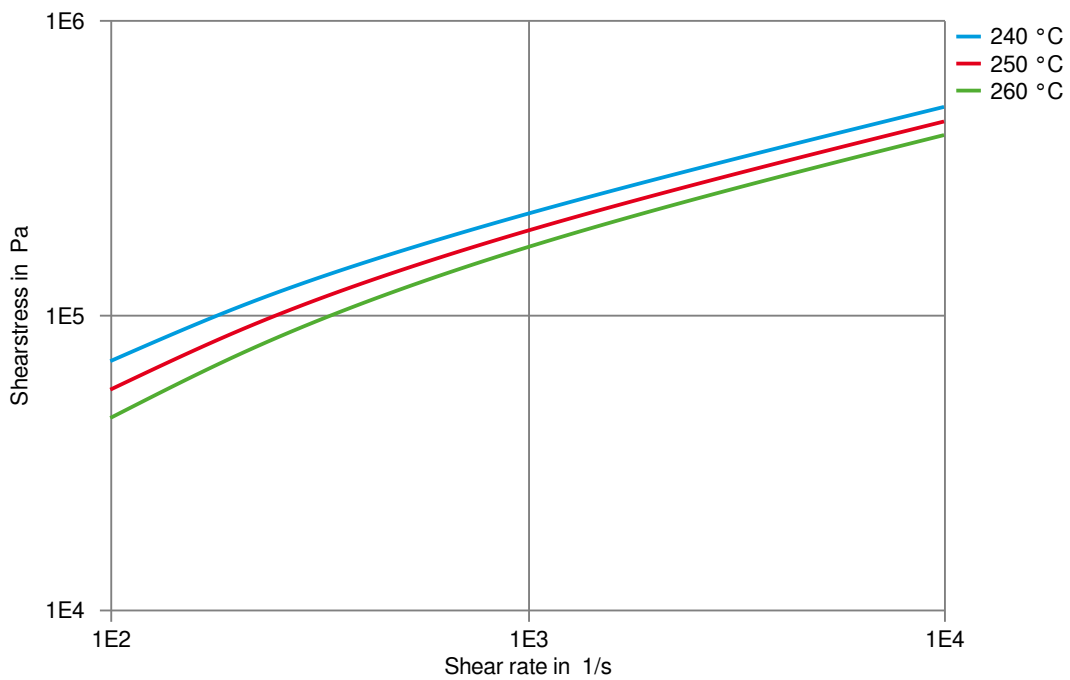

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN


Stress-strain
(measured on Crastin® LW9020 BK580)

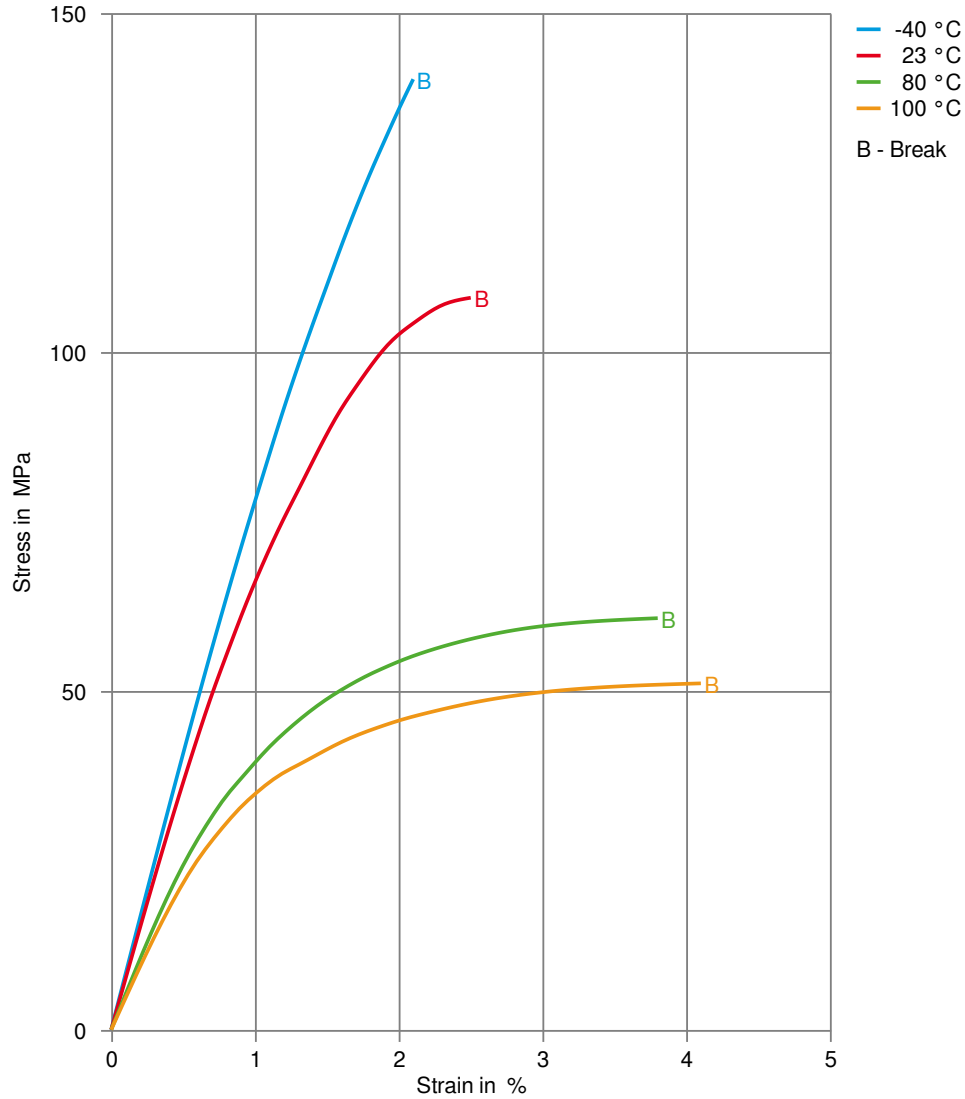

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN


Secant modulus-strain
(measured on Crastin® LW9020 BK580)

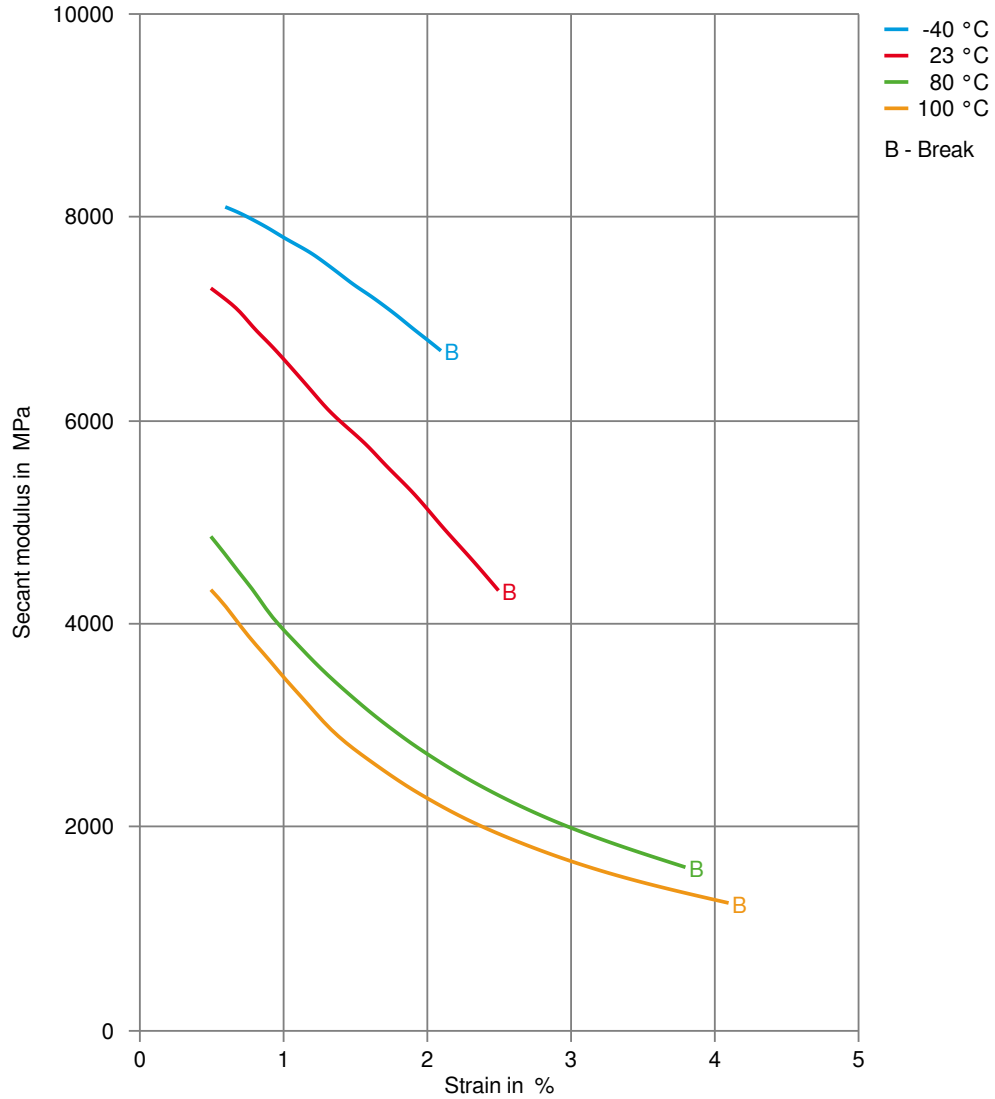

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN

Specific volume-temperature (pvT)

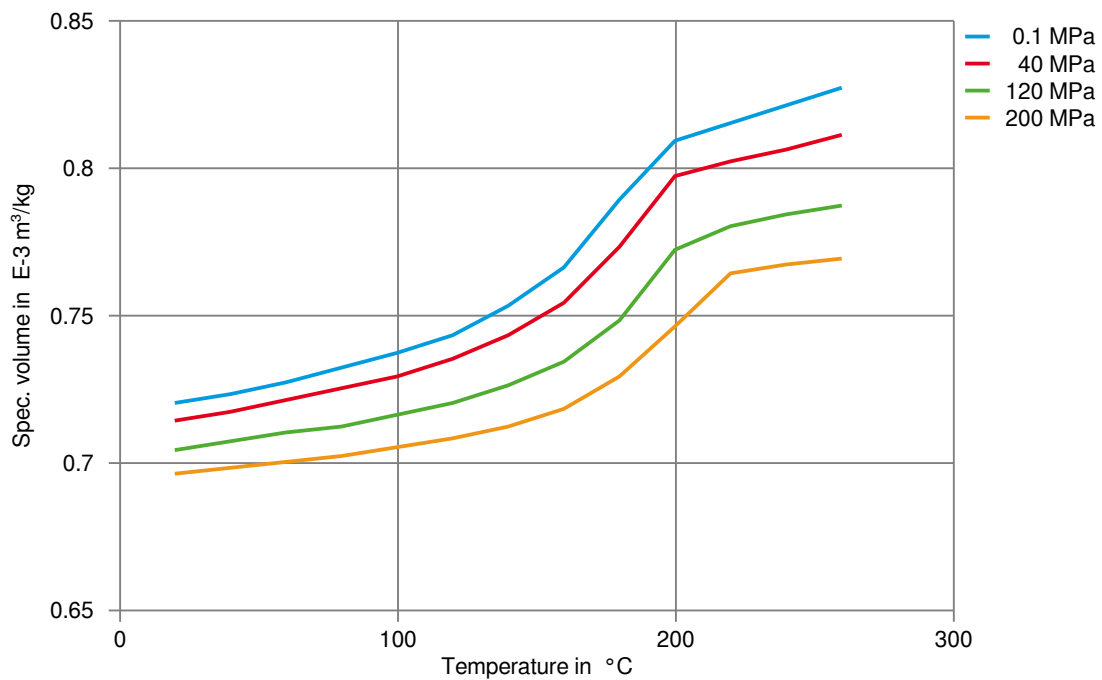

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN

Chemical Media Resistance

Acids

- ✓ Acetic Acid (5% by mass), 23 °C
- ✓ Citric Acid solution (10% by mass), 23 °C
- ✓ Lactic Acid (10% by mass), 23 °C
- ✗ Hydrochloric Acid (36% by mass), 23 °C
- ✗ Nitric Acid (40% by mass), 23 °C
- ✗ Sulfuric Acid (38% by mass), 23 °C
- ✗ Sulfuric Acid (5% by mass), 23 °C
- ✗ Chromic Acid solution (40% by mass), 23 °C

Bases

- ✗ Sodium Hydroxide solution (35% by mass), 23 °C
- ✓ Sodium Hydroxide solution (1% by mass), 23 °C
- ✓ Ammonium Hydroxide solution (10% by mass), 23 °C

Alcohols

- ✓ Isopropyl alcohol, 23 °C
- ✓ Methanol, 23 °C
- ✓ Ethanol, 23 °C

Hydrocarbons

- ✓ n-Hexane, 23 °C
- ✓ Toluene, 23 °C
- ✓ iso-Octane, 23 °C

Ketones

- ✓ Acetone, 23 °C

Ethers

- ✓ Diethyl ether, 23 °C

Mineral oils

- ✓ SAE 10W40 multigrade motor oil, 23 °C
- ✗ SAE 10W40 multigrade motor oil, 130 °C
- ✗ SAE 80/90 hypoid-gear oil, 130 °C
- ✓ Insulating Oil, 23 °C

Standard Fuels

- ✗ ISO 1817 Liquid 1 - E5, 60 °C
 - ✗ ISO 1817 Liquid 2 - M15E4, 60 °C
 - ✗ ISO 1817 Liquid 3 - M3E7, 60 °C
 - ✗ ISO 1817 Liquid 4 - M15, 60 °C
 - ✓ Standard fuel without alcohol (pref. ISO 1817 Liquid C), 23 °C
 - ✓ Standard fuel with alcohol (pref. ISO 1817 Liquid 4), 23 °C
 - ✓ Diesel fuel (pref. ISO 1817 Liquid F), 23 °C
 - ✓ Diesel fuel (pref. ISO 1817 Liquid F), 90 °C
 - ✗ Diesel fuel (pref. ISO 1817 Liquid F), >90 °C
-

Crastin® LW9020SF BK580

THERMOPLASTIC POLYESTER RESIN

Salt solutions

- ✓ Sodium Chloride solution (10% by mass), 23°C
- ✓ Sodium Hypochlorite solution (10% by mass), 23°C
- ✓ Sodium Carbonate solution (20% by mass), 23°C
- ✓ Sodium Carbonate solution (2% by mass), 23°C
- ✓ Zinc Chloride solution (50% by mass), 23°C

Other

- ✓ Ethyl Acetate, 23°C
- ✗ Hydrogen peroxide, 23°C
- ✗ DOT No. 4 Brake fluid, 130°C
- ✗ Ethylene Glycol (50% by mass) in water, 108°C
- ✓ 1% nonylphenoxy-polyethyleneoxy ethanol in water, 23°C
- ✓ 50% Oleic acid + 50% Olive Oil, 23°C
- ✓ Water, 23°C
- ✗ Water, 90°C
- ✓ Phenol solution (5% by mass), 23°C

Symbols used:

- ✓ possibly resistant
Defined as: Supplier has sufficient indication that contact with chemical can be potentially accepted under the intended use conditions and expected service life. Criteria for assessment have to be indicated (e.g. surface aspect, volume change, property change).
 - ✗ not recommended - see explanation
Defined as: Not recommended for general use. However, short-term exposure under certain restricted conditions could be acceptable (e.g. fast cleaning with thorough rinsing, spills, wiping, vapor exposure).
-