

Rynite® 550HTE BK503

THERMOPLASTIC POLYESTER RESIN

Rynite® 550HTE BK503 is a 50% glass reinforced modified polyethylene terephthalate resin with excellent high temperature dielectric properties

Product information

Resin Identification	PET-GF50	ISO 1043
Part Marking Code	>PET-GF50<	ISO 11469

Rheological properties

Melt volume-flow rate	6.5 cm ³ /10min	ISO 1133
Temperature	280 °C	
Load	10 kg	
Viscosity number	57 cm ³ /g	ISO 307, 1628
Moulding shrinkage, parallel	0.2 %	ISO 294-4, 2577
Moulding shrinkage, normal	0.7 %	ISO 294-4, 2577

Typical mechanical properties

Tensile modulus	18000 MPa	ISO 527-1/-2
Tensile stress at break, 5mm/min	190 MPa	ISO 527-1/-2
Tensile strain at break, 5mm/min	1.8 %	ISO 527-1/-2
Flexural modulus	16000 MPa	ISO 178
Flexural strength	280 MPa	ISO 178
Charpy impact strength, 23°C	65 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	11 kJ/m ²	ISO 179/1eA
Poisson's ratio	0.33	

Thermal properties

Melting temperature, 10°C/min	251 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	95 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	235 °C	ISO 75-1/-2
Coefficient of linear thermal expansion (CLTE), parallel	16 E-6/K	ISO 11359-1/-2
Coefficient of linear thermal expansion (CLTE), normal	81 E-6/K	ISO 11359-1/-2

Electrical properties

Electric strength	30 kV/mm	IEC 60243-1
-------------------	----------	-------------

Physical/Other properties

Density	1750 kg/m ³	ISO 1183
Density of melt	1560 kg/m ³	

Rynite® 550HTE BK503

THERMOPLASTIC POLYESTER RESIN

Injection

Drying Recommended	yes
Drying Temperature	120 °C
Drying Time, Dehumidified Dryer	4 - 6 h
Processing Moisture Content	≤0.01 ^[1] %
Melt Temperature Optimum	285 °C
Min. melt temperature	280 °C
Max. melt temperature	300 °C
Mold Temperature Optimum	130 °C
Min. mould temperature	120 °C
Max. mould temperature	140 ^[2] °C
Ejection temperature	201 °C

[1]: At levels above 0.01%, strength and toughness will decrease, even though parts may not exhibit surface defects.

[2]: (6mm - 1mm thickness)

Characteristics

Processing

Injection Moulding

Additional information

Injection molding


When lower mold temperatures are used, the initial warpage and shrinkage will be lower, but the surface appearance will be poorer and the dimensional change may be greater when parts are subsequently heated.

Higher temperature settings for the rear of the barrel will minimize glass fiber attrition, though overall barrel residence time should be considered.

Rynite® 550HTE BK503

THERMOPLASTIC POLYESTER RESIN


Dynamic Tensile modulus-temperature

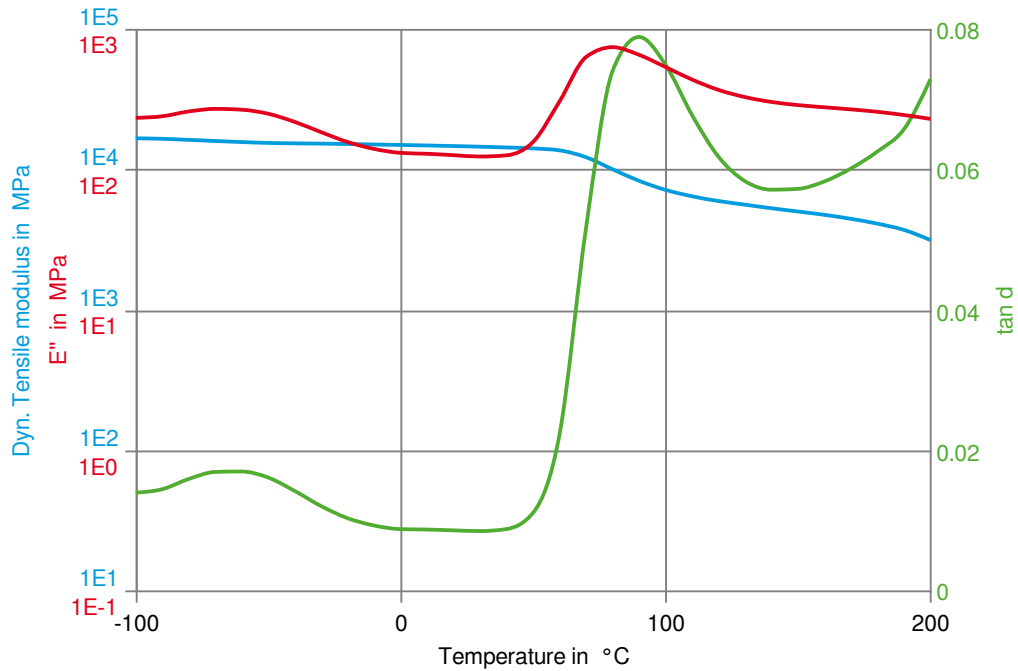

Rynite® 550HTE BK503

THERMOPLASTIC POLYESTER RESIN


Stress-strain

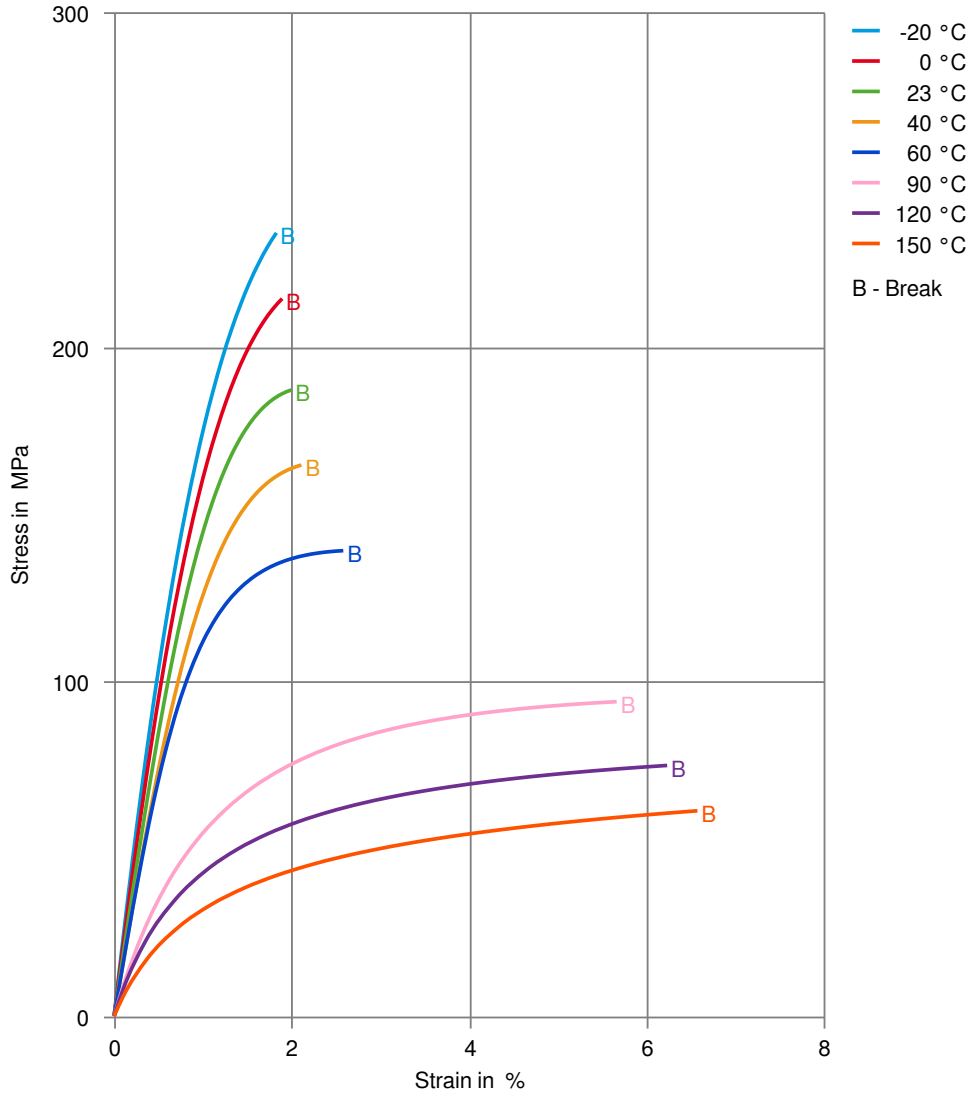

Rynite® 550HTE BK503

THERMOPLASTIC POLYESTER RESIN

Secant modulus-strain

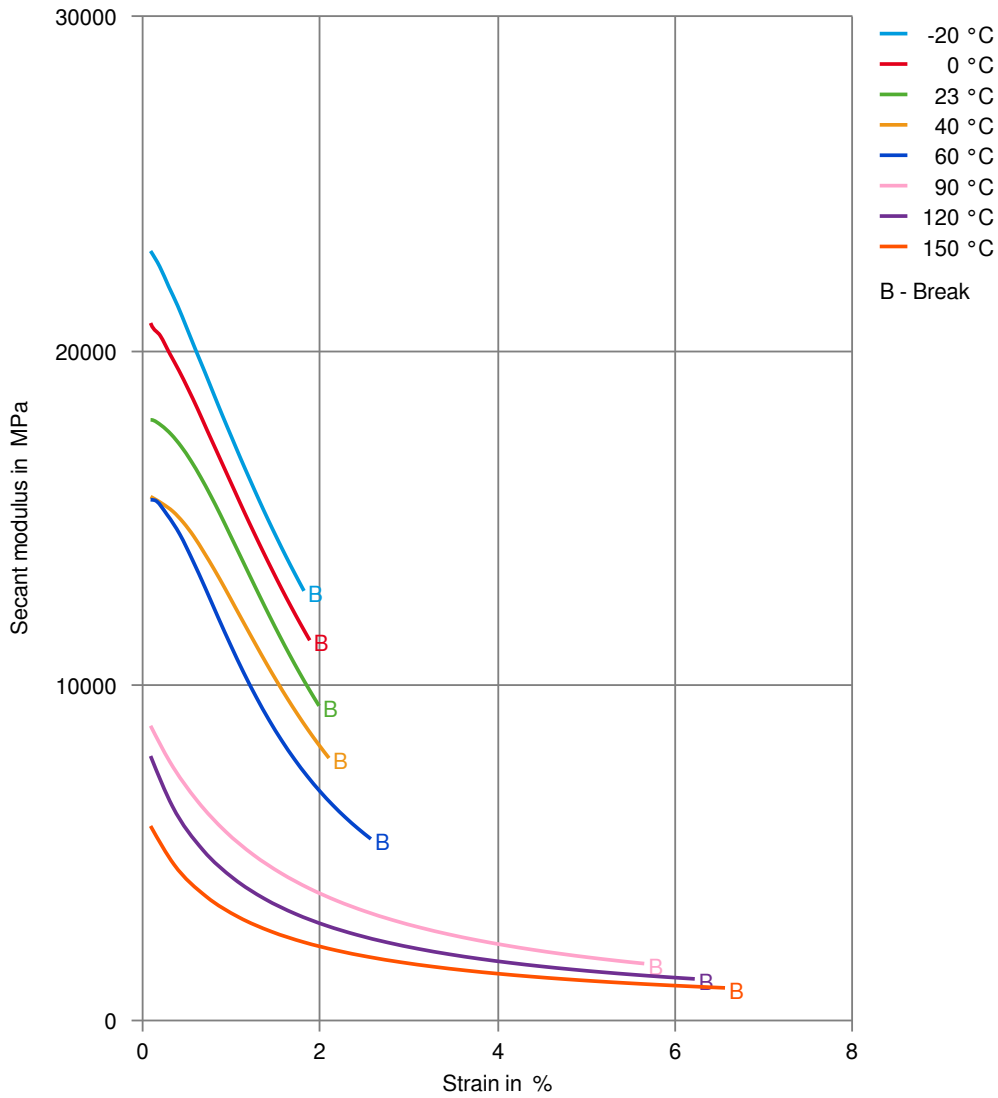

Rynite® 550HTE BK503

THERMOPLASTIC POLYESTER RESIN

Tensile modulus-temperature

