

# HOSTAFORM® C 9021 TF

## HOSTAFORM®

Chemical abbreviation according to ISO 1043-1: POM Molding compound ISO 29988- POM-K, M-GNS, 02-002 POM copolymer Injection molding type, modified with PTFE; good chemical resistance to solvents, fuel and strong alkalis as well as good hydrolysis resistance; high resistance to thermal and oxidative degradation; for sliding combinations with very low coefficient of friction. UL-registration in natural and a thickness more than 1.57 mm as UL 94 HB, temperature index UL 746 B electrical 105 °C, mechanical 95 °C (tensile impact) and 100 °C (tensile). Burning rate ISO 3795 and FMVSS 302 < 100 mm/min for a thickness more than 1 mm. Ranges of applications: For sliding combinations with very low coefficient of friction. FMVSS = Federal Motor Vehicle Safety Standard (USA) UL = Underwriters Laboratories (USA)

### Product information

Resin Identification	POM+PTFE	ISO 1043
Part Marking Code	>POM+PTFE<	ISO 11469

### Rheological properties

Melt volume-flow rate	6 cm <sup>3</sup> /10min	ISO 1133
Temperature	190 °C	
Load	2.16 kg	
Moulding shrinkage, parallel	2.0 <sup>[1]</sup> %	ISO 294-4, 2577
Moulding shrinkage, normal	1.7 <sup>[1]</sup> %	ISO 294-4, 2577
[1]: @ 195 °C		

### Typical mechanical properties

Tensile modulus	2500 MPa	ISO 527-1/-2
Tensile stress at yield, 50mm/min	48 MPa	ISO 527-1/-2
Tensile strain at yield, 50mm/min	10 %	ISO 527-1/-2
Nominal strain at break	16 %	ISO 527-1/-2
Flexural modulus	2400 MPa	ISO 178
Tensile creep modulus, 1h	2100 MPa	ISO 899-1
Tensile creep modulus, 1000h	1200 MPa	ISO 899-1
Charpy impact strength, 23 °C	60 kJ/m <sup>2</sup>	ISO 179/1eU
Charpy impact strength, -30 °C	60 kJ/m <sup>2</sup>	ISO 179/1eU
Charpy notched impact strength, 23 °C	4 kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength, -30 °C	4 kJ/m <sup>2</sup>	ISO 179/1eA
Ball indentation hardness, H 358/30	120 MPa	ISO 2039-1
Poisson's ratio	0.38 <sup>[C]</sup>	
[C]: Calculated		

### Thermal properties

Melting temperature, 10 °C/min	166 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	98 °C	ISO 75-1/-2
Coefficient of linear thermal expansion (CLTE), parallel	110 E-6/K	ISO 11359-1/-2

### Flammability

Burning Behav. at 1.5mm nom. thickn.	HB class	IEC 60695-11-10
Thickness tested	1.6 mm	IEC 60695-11-10
Burning Behav. at thickness h	HB class	IEC 60695-11-10
Thickness tested	3.18 mm	IEC 60695-11-10
UL recognition	yes	UL 94

# HOSTAFORM® C 9021 TF

## HOSTAFORM®

### Electrical properties

Relative permittivity, 100Hz	3.7	IEC 62631-2-1
Relative permittivity, 1MHz	3.7	IEC 62631-2-1
Dissipation factor, 100Hz	20 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	80 E-4	IEC 62631-2-1
Volume resistivity	1E12 Ohm.m	IEC 62631-3-1
Surface resistivity	1E14 Ohm	IEC 62631-3-2
Electric strength	33 kV/mm	IEC 60243-1
Comparative tracking index	600	IEC 60112

### Physical/Other properties

Humidity absorption, 2mm	0.2 %	Sim. to ISO 62
Water absorption, 2mm	0.65 %	Sim. to ISO 62
Density	1510 kg/m <sup>3</sup>	ISO 1183

### Injection

Drying Recommended	no
Drying Temperature	100 °C
Drying Time, Dehumidified Dryer	3 - 4 h
Processing Moisture Content	≤0.2 %
Melt Temperature Optimum	195 °C
Min. melt temperature	190 °C
Max. melt temperature	200 °C
Screw tangential speed	≤0.3 m/s
Mold Temperature Optimum	100 °C
Min. mould temperature	80 °C
Max. mould temperature	120 °C
Hold pressure range	60 - 120 MPa
Back pressure	2 MPa
Ejection temperature	139 °C

### Characteristics

Processing	Injection Moulding, Other Extrusion
Delivery form	Pellets
Additives	Release agent
Special characteristics	Low wear / Low friction

### Additional information

Injection molding

### Preprocessing

General drying is not necessary due to low moisture absorption of the resin.

In case of bad storage conditions (water contact or condensed water) the use of a recirculating air dryer (100 to 120 °C / max. 40 mm layer / 3 to 6 hours) is recommended.

# HOSTAFORM® C 9021 TF

## HOSTAFORM®

Max. Water content 0,2 %

### Processing

Standard injection moulding machines with three phase (15 to 25 D) plasticating screws will fit.

### Postprocessing

Conditioning e.g. moisturizing is not necessary.

### Pre-Drying

Drying is not normally required. If material has come in contact with moisture through improper storage or handling or through regrind use, drying may be necessary to prevent splay and odor problems.

### Storage

The product can then be stored in standard conditions until processed.

### Processing Notes


### Automotive

OEM	STANDARD	ADDITIONAL INFORMATION
BMW	GS93016	
Bosch	N28 BN22-X017	Natural
Continental	TST N 055 54.18	
Hyundai	MS237-05 Type D	
Mercedes-Benz	DBL5410	(5410.00)
Nissan	POM(0xx)-lxx-1	
SAIC Motor	SMTC 5 310 020	

# HOSTAFORM® C 9021 TF

HOSTAFORM®


## Stress-strain

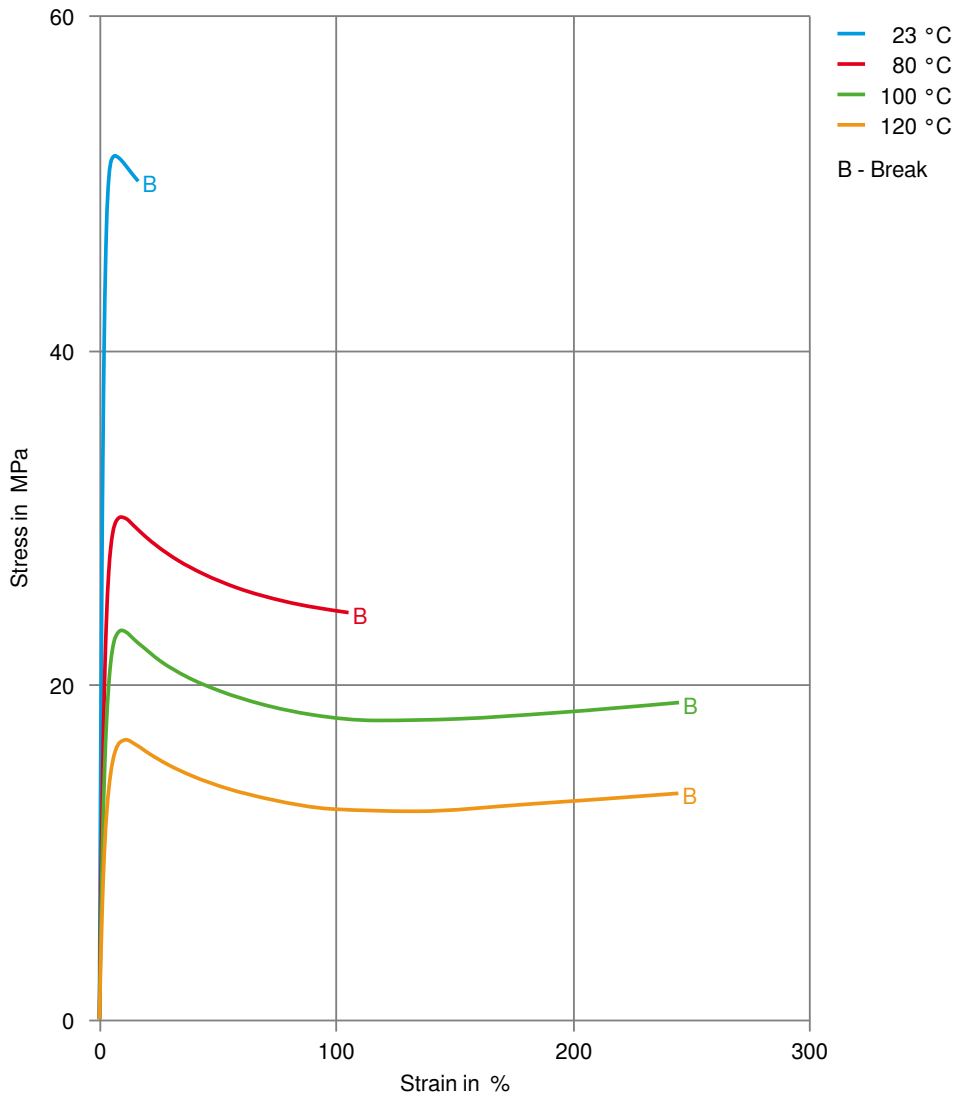

# HOSTAFORM® C 9021 TF

HOSTAFORM®


## Secant modulus-strain

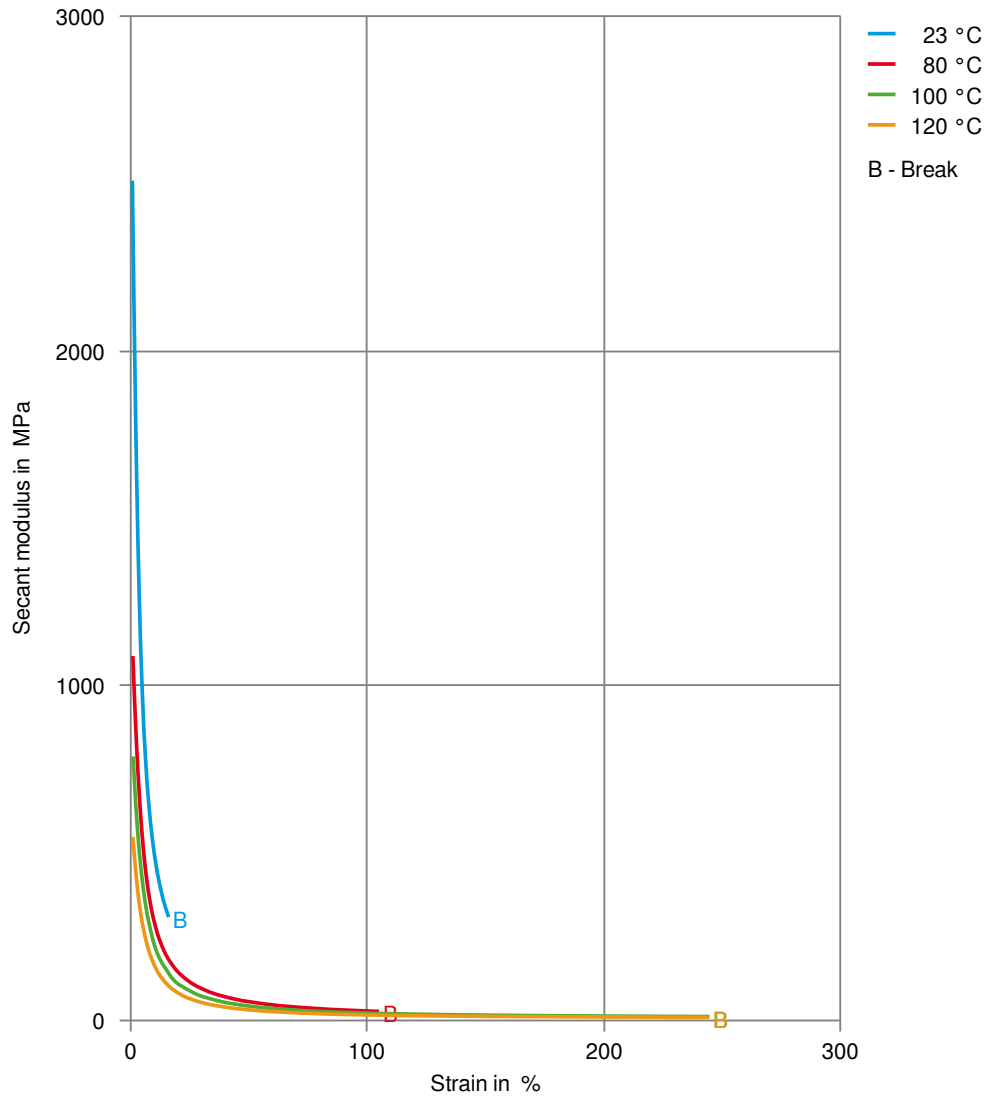

# HOSTAFORM® C 9021 TF

HOSTAFORM®


Stress-strain (isochronous) 23°C

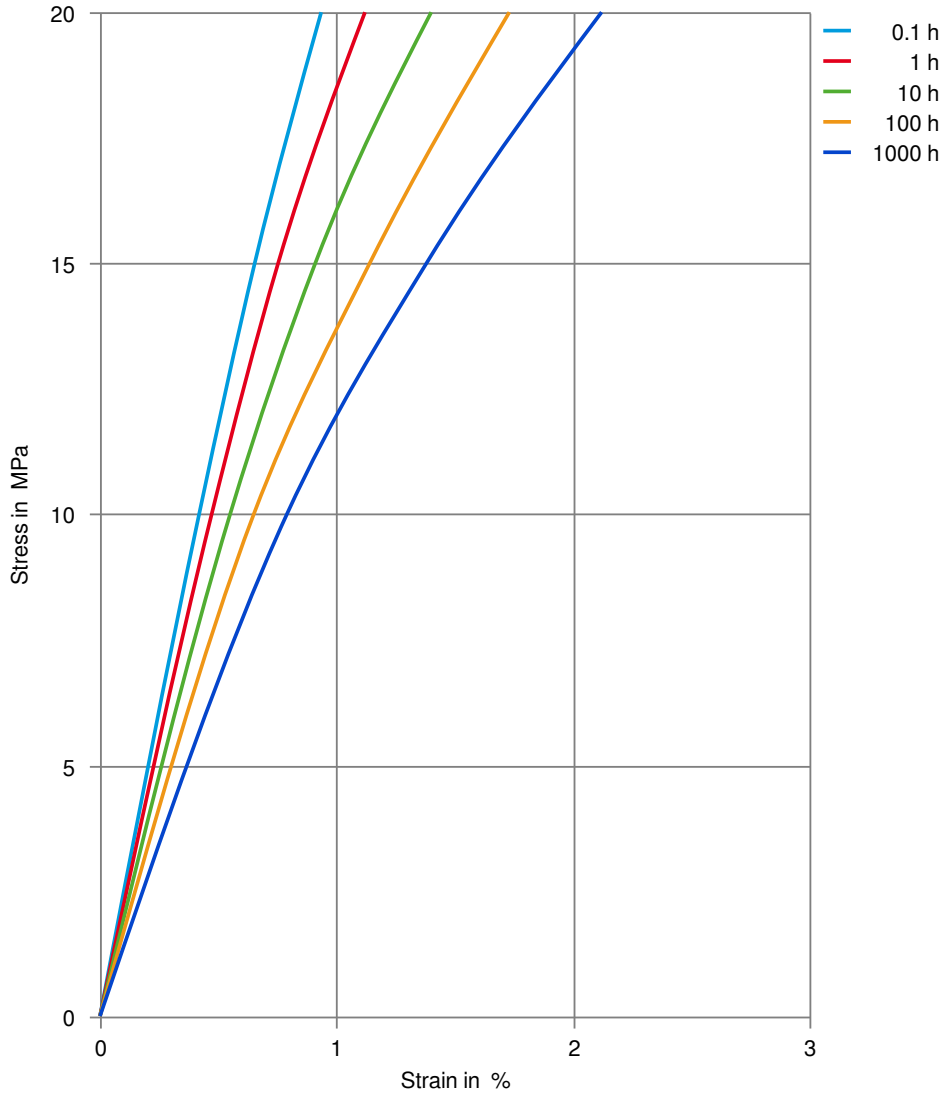

# HOSTAFORM® C 9021 TF

HOSTAFORM®


Creep modulus-time 23°C

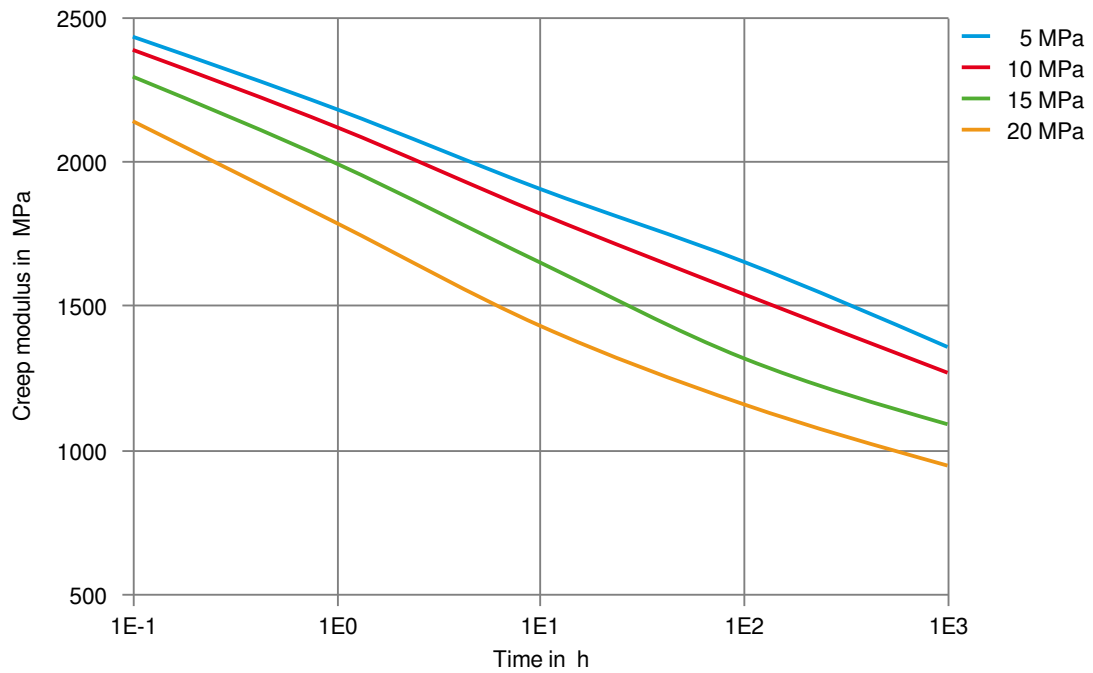

# HOSTAFORM® C 9021 TF

HOSTAFORM®

Creep modulus-time 23°C

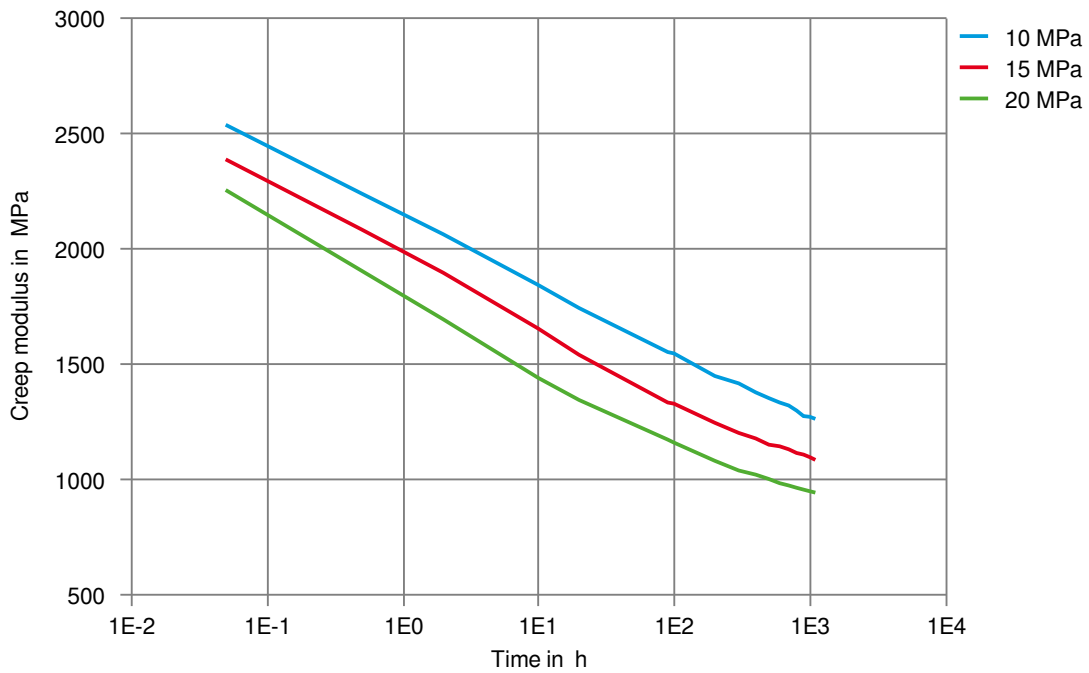

# HOSTAFORM® C 9021 TF

HOSTAFORM®

Creep strain-time 23°C

